

Solid-that-Flows Picture of Glass-Forming Liquids

Jeppe C. Dyre



Cite This: *J. Phys. Chem. Lett.* 2024, 15, 1603–1617




Read Online

ACCESS |

Metrics & More

Article Recommendations

ABSTRACT: This perspective article reviews arguments that glass-forming liquids are different from those of standard liquid-state theory, which typically have a viscosity in the mPa·s range and relaxation times on the order of picoseconds. These numbers grow dramatically and become $10^{12} - 10^{15}$ times larger for liquids cooled toward the glass transition. This translates into a qualitative difference, and below the “solidity length” which is roughly one micron at the glass transition, a glass-forming liquid behaves much like a solid. Recent numerical evidence for the solidity of ultraviscous liquids is reviewed, and experimental consequences are discussed in relation to dynamic heterogeneity, frequency-dependent linear-response functions, and the temperature dependence of the average relaxation time.

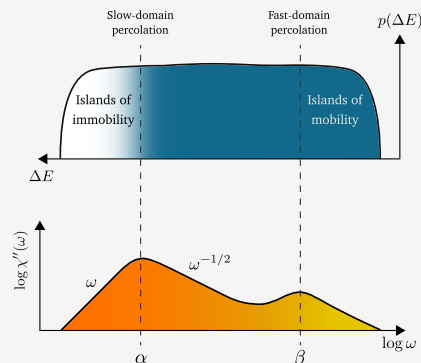

Liquids flow and solids do not, according to the conventional wisdom. In reality, any solid does flow when subjected to an external force^{1–7} while, on the other hand, an extremely viscous liquid only flows very slowly. Should one think of the latter as an ordinary liquid like water or a molten metal, merely with a much higher viscosity, or more as a solid that flows?^{8,9} This question is important for liquids approaching the glass transition, where the viscosity is $10^{12} - 10^{15}$ times larger than that of ordinary liquids.

A glass is usually made by supercooling a liquid fast enough to avoid crystallization. It is a solid that has inherited the liquid’s disorder and macroscopic isotropy. While some substances like pure metals require extremely high cooling rates to form glasses, others, e.g., many organic liquids, are easily supercooled and, in fact, often difficult to crystallize. Because all substances can form glasses, glass may be regarded as the fourth state of conventional matter.⁹ With only few exceptions like the silicates, a liquid’s viscosity η at the melting temperature T_m is within one or two orders of magnitude of that of water, $\eta \sim 10^{-3}$ Pa·s. Upon supercooling, the viscosity increases dramatically, and for typical cooling rates of order K/min one finds $\eta \sim 10^{12}$ Pa·s at the glass transition temperature T_g (brief introductions to the glass transition are given in refs 9–13 and more comprehensive reviews in refs 14–25).

The glass transition is continuous and not a genuine phase transition, although T_g is fairly well-defined for a given cooling rate, typically within 1%. At T_g the system falls out of metastable equilibrium because the time to reach equilibrium after an external disturbance, the so-called α relaxation time τ_ω exceeds the laboratory time scale. By the fluctuation–dissipation theorem, τ_α is also the characteristic time of the equilibrium fluctuations. This quantity is termed the Maxwell

relaxation time, and in the Maxwell model of viscoelasticity,^{9,26,27} τ_α is given by

$$\tau_\alpha = \frac{\eta}{G_\infty} \quad (1)$$

in which G_∞ is the high-frequency plateau shear modulus corresponding to MHz frequencies and above (sometimes denoted by G_p). In this expression, the temperature dependence of G_∞ is insignificant, so upon cooling, τ_α increases roughly proportionally to η . With $G_\infty \sim 10^9$ Pa, the typical ordinary liquid viscosity of 10^{-3} Pa·s corresponds to $\tau_\alpha \sim 10^{-12}$ s, which is comparable to vibration (phonon) times. On the other hand, equating τ_α to the typical cooling time for producing a glass $\sim 10^3$ s leads to $\eta \sim 10^{12}$ Pa·s.

A note on terminology: The term “glass” is used below whenever a highly viscous liquid is not in thermodynamic equilibrium, while “liquid” is reserved for a system in (metastable) equilibrium, i.e., one that is fully characterized by pressure and temperature with no memory of its past. The terms “glass-forming liquid” and “ultraviscous liquid” are used synonymously, reflecting the fact that once a liquid has been supercooled to the ultraviscous state by avoiding crystallization, glass formation is inevitable upon continued cooling.


Ordinary Liquids. Consider a pure substance above its melting temperature. As a crude approximation, one may adopt

Received: November 24, 2023

Revised: January 12, 2024

Accepted: January 17, 2024

Published: February 2, 2024



the hard-sphere (HS) model consisting of identical particles that do not interact, except by never overlapping (Figure 1).

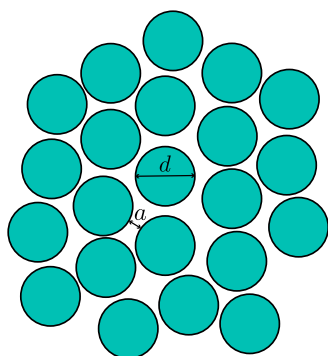


Figure 1. Hard-sphere liquid in two dimensions. There are frequent collisions because the particles almost touch. For a rough order-of-magnitude estimate of the system's transport properties, however, one can assume that $a \sim d$.

Although this model is highly idealized, it is quite successful in reproducing the structure and dynamics of simple liquids.^{28,29} Temperature plays no role in the HS model except for determining the average particle velocity, i.e., the relevant time scale. The only nontrivial thermodynamic variable is density (packing fraction). The HS model may be regarded as a mathematician's idealized liquid; an alternative generic model in which temperature does play a role is the EXP system defined by the exponential repulsive pair potential.^{30–32}

In the HS liquid, each particle is close to several others (Figure 1), and the frequent particle collisions result in an erratic particle motion. This is different from what happens in the gas phase in which the mean-free path between collisions is much larger than the particle diameter. It is useful to discuss the physics of the HS liquid in terms of two diffusion coefficients: the particle-diffusion coefficient D_{par} and the transverse-momentum diffusion coefficient D_{mom} . The latter is the kinematic viscosity of the Navier–Stokes equation, $D_{\text{mom}} = \eta/\rho$ in which ρ is the mass density,³³ while D_{par} is defined from the long-time mean-square particle displacement via $\langle \Delta x^2(t) \rangle = 2D_{\text{par}}t$.

Writing $A \sim B$ to indicate that A and B are within one or two decades of each other, the HS liquid is characterized by

$$D_{\text{par}} \sim D_{\text{mom}} \quad (2)$$

This applies not only for HS but for all ordinary liquids. D_{par} may be estimated by considering a random walk, leading to $D_{\text{par}} \sim d^2/\tau_{\alpha}$. Typical experimental values of D_{par} and D_{mom} are of order 10^{-7} m²/s, which may be arrived at from $d \sim 10^{-10}$ m and $\tau_{\alpha} \sim 10^{-13}$ s or from $D_{\text{mom}} = \eta/\rho$ with $\eta \sim 10^{-3}$ Pa·s and $\rho \sim 10^3$ kg/m³.

When the viscosity of a glass-forming liquid upon cooling increases by many orders of magnitude, surprisingly little structural change takes place.¹⁹ This means that Figure 1 is still a fairly good representation with regard to structure, which raises the following question: how should one think of a liquid with the extremely slow dynamics characterizing the approach to the glass transition?

Ultraviscous Liquids. In thermal equilibrium, atoms/molecules have velocities proportional to the square root of the temperature, but this motion does not necessarily imply lasting particle displacement. In a crystal, for instance, all thermal

motion goes into vibrations around the equilibrium positions. One likewise expects effective particle motion in an ultraviscous liquid to be minute because, in order to move a particle with a certain velocity, a force is required that is proportional to the viscosity. Indeed, according to the Stokes–Einstein relation, D_{par} is inversely proportional to the viscosity.^{29,34} Although derived by reference to macroscopic hydrodynamics, the Stokes–Einstein relation works well for simple liquids even on the molecular scale.³⁵ The relation is violated by 1–3 orders of magnitude for liquids approaching the glass transition,^{36–39} but this does not alter the fact that when viscosity increases upon cooling, D_{par} decreases roughly as much: $D_{\text{par}} \propto \eta^{-x}$ with $0.8 \leq x \leq 1.0$.^{40–42} Thus, when the viscosity—and thereby D_{mom} —increases by a factor of 10^{15} by cooling from T_m to T_g , D_{par} at the same time decreases enormously. Interestingly, the heat-diffusion coefficient D_{heat} changes only insignificantly upon cooling, even into the glassy state.^{43,44} To summarize, an ultraviscous liquid is characterized by

$$D_{\text{par}} \ll D_{\text{heat}} \ll D_{\text{mom}} \quad (3)$$

Flow Events. Since effective particle motion is exceedingly slow in an ultraviscous liquid while velocities are not, most motion must go into vibrations. Two possible scenarios can realize this. The vibrations can take place around average positions that change continuously but extremely slowly. Alternatively, sudden rare localized “flow events” rearrange a handful of particles. Experiments on colloidal,²⁰ molecular,⁴⁸ and metallic⁴⁹ glass-forming liquids, as well as computer simulations,⁴⁷ favor the latter scenario. This does not mean that very slow position changes are absent;⁵⁰ they do take place and are important for the physics. According to the *solid-that-flows* picture as detailed below, however, these minor displacements are an *effect* of flow events taking place in a solid-like structure.

It is an old idea that particle motion in a glass-forming liquid proceeds via flow events. In his seminal 1948 review, Kauzmann referred to flow events as “jumps of molecular units of flow between different positions of equilibrium in the liquid's quasicrystalline lattice”.⁵¹ Mooney in 1957 poetically referred to a flow event as “a quantum of liquid flow”,²⁶ and many subsequent papers have embraced this picture of viscous liquid dynamics.^{52–57} The physics, of course, lies in what determines the energy barriers of flow events, how these events correlate in space and time, and how they control physical properties.

Why are flow events rare in an ultraviscous liquid? This was reflected upon by Goldstein in his famous 1969 paper.⁵⁸ He identified Kauzmann's “positions of equilibrium” with minima of the potential-energy function. Flow events are rare because the barriers to be overcome on going from one minimum to another are much larger than $k_B T$. Potential-energy minima are nowadays referred to as “inherent states”.⁵⁹ Goldstein's picture is that the dynamics of an ultraviscous liquid involves numerous vibrations around an inherent state. These vibrations do not contribute to the slow dynamics and may be eliminated by focusing on the “inherent dynamics” defined as the time sequence of inherent states.^{47,60}

Anticipating that an ultraviscous liquid is like a solid on short length scales, any flow event leads to minor deformations in its surroundings.^{61–63} These may be detected, e.g., by NMR experiments.⁶⁴ Far from a flow event linear elasticity applies, and in 3D the induced particle motion scales as $1/r^2$ for $r \rightarrow \infty$

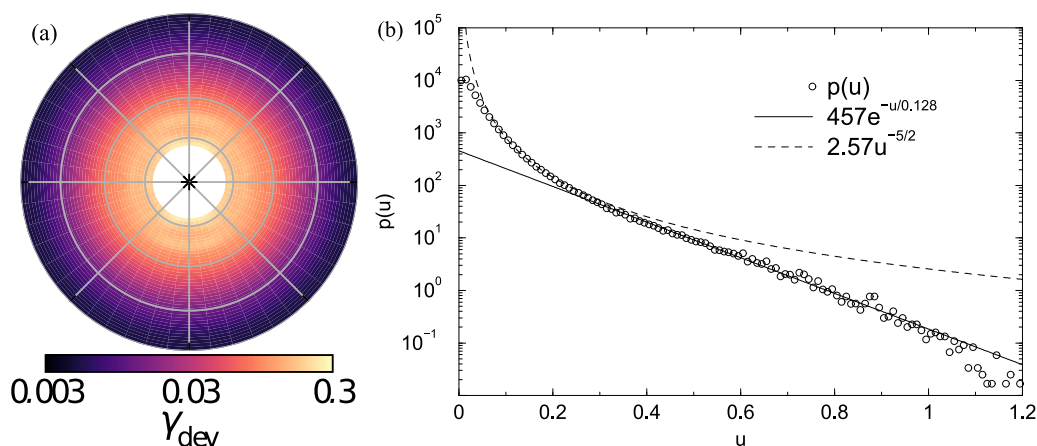


Figure 2. Displacements induced by a flow event in a glass-forming liquid. (a) Average deviatoric strain displacement in the surroundings of flow events in simulations of a 2D polydisperse glass-forming liquid; the radial axis is logarithmic with two units corresponding to a factor of 10. The data conform to the long-range decay $\propto 1/r^2$ predicted by solid-state elasticity theory. Reproduced from ref 45. Copyright 2021 Authors, licensed under a Creative Commons License. (b) Displacement probability, $p(u)$, in the surroundings of flow events of a 3D binary glass-forming liquid. The vast majority of displacements are small and conform to $p(u) \propto u^{-5/2}$ (dashed curve), which is a consequence of the solid-state elasticity-theory prediction $u \propto 1/r^2$ for $r \rightarrow \infty$.^{46,47} The limited number of particles of this early simulation ($N = 500$) accounts for the deviation from the dashed curve at small u . Reproduced from ref 47. Copyright 2000 AIP Publishing.

where r is the distance to the flow event⁶⁵ (Figure 2). To show this, one uses the mechanical-equilibrium requirement that the time-averaged force on each particle is zero both before and after a flow event. A single flow event's effects on the surroundings may be reproduced by imagining external forces acting on a small surface surrounding it.^{66–68} By momentum conservation, each of these forces leads to a momentum flow into the surroundings $\propto 1/r^2$ for $r \rightarrow \infty$. Since the forces sum to zero, this implies an overall momentum flow (stress tensor) that is the spatial derivative, i.e., $\propto 1/r^3$. According to elasticity theory,⁶⁵ the stress tensor change is linearly related to the strain field, which is formed from derivatives of the displacement field that consequently must scale as $\propto 1/r^2$.⁶⁹ In 2D, the stress and strain fields induced by a flow event scale as $\propto 1/r^2$ for $r \rightarrow \infty$ and the particle displacements as $\propto 1/r$.

Solidity Length. The above and Figure 2 suggest that the physics of an ultraviscous liquid is reminiscent of that of a solid. Real-life solids are mostly crystalline, with grain boundaries separating small crystals containing point defects. In thermal equilibrium, however, the solid state of any pure substance is a single crystal with no line defects or grain boundaries, while a few point defects like vacancies and interstitials, i.e., missing or extra atoms, are present.⁷⁰ Point defects can jump to neighboring positions by overcoming a barrier much larger than $k_B T$, just like flow events in ultraviscous liquids.

The effect of a flow event on its surroundings is not instantaneous due to the finite sound velocity. After a flow event, others take place that likewise send out spherical “waves” of minor adjustments to the particle positions (Figure 3). Far from the original flow event, the adjustments originating from many other flow events interfere with and increasingly smear out the effect of the original flow event. We proceed to estimate the length scale beyond which this significantly dampens the effects of a flow event, which defines the system's “solidity length” l_s . The system is solid-like on length scales smaller than l_s , but not on larger length scales. A related concept is the “shear penetration depth” quantifying how far an external shear disturbance penetrates into the liquid.⁷¹

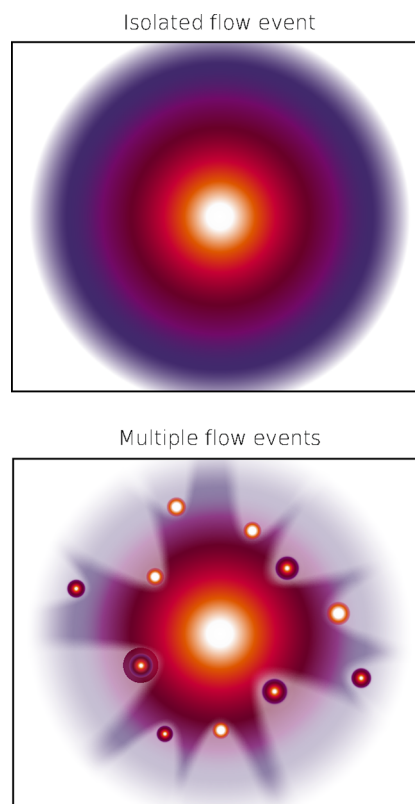


Figure 3. An isolated flow event and its screening by subsequent nearby flow events (artist's impression). The radius of the sphere inside which the effects of the original flow event are felt in full defines the solidity length l_s .

To estimate l_s , we make the crude approximation that the average time between two flow events involving a given molecule is τ_a . If a is the average intermolecular distance, a sphere of radius l_s contains on order $N \cong (l_s/a)^3$ sites for potential flow events. Flow events are not independent and uncorrelated, but for simplicity we ignore this and estimate the average time between two flow events within the sphere to be

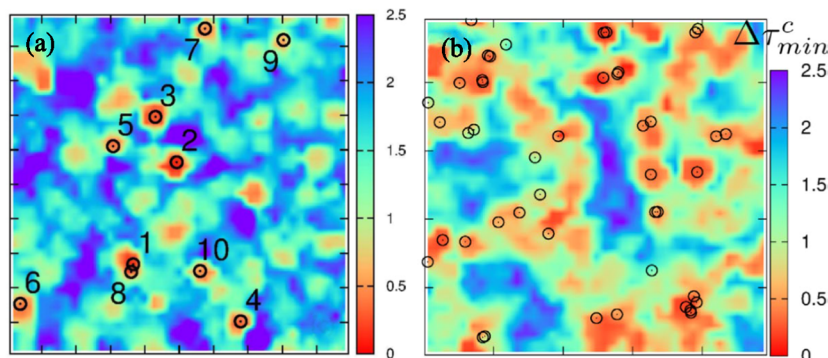


Figure 4. Soft spots in 2D systems. (a) Softness probed as the local yield stress of a binary Lennard-Jones glass in which red and blue mark soft and hard regions, respectively. The numbered points give the time sequence of plastic flow events when the system is sheared at zero temperature, which are located at the soft spots. Reproduced from ref 94. Copyright 2018 American Physical Society. (b) Analogous results for an equilibrium ultraviscous 2D liquid in which softness is probed by the local yield stress of the system's inherent state, i.e., potential-energy minimum, at a specific time. The circles mark the first 50 subsequent flow events. Like the plastic flow events of the glass in (a), these preferably take place at soft spots. Reproduced from ref 95. Copyright 2022 American Physical Society.

τ_α/N . The solidity length is determined by requiring that this equals the time it takes a sound wave to travel l_s , which is l_s/c where c is the sound velocity,⁴⁶ leading to

$$l_s^4 \cong ca^3\tau_\alpha \quad (4)$$

For an ordinary liquid, the derivation makes little sense, but if one nevertheless substitutes $c \sim 10^3$ m/s, $a \sim 10^{-10}$ m, and $\tau_\alpha \sim 10^{-13}$ s into eq 4, the result is $l_s \sim 10^{-10}$ m. For a liquid approaching the glass transition, $\tau_\alpha \sim 10^3$ s leads to $l_s \sim 10^{-6}$ m. This length is much larger than those discussed in connection with dynamic heterogeneities of glass-forming liquids.^{72–75} Note that the derivation of eq 4 is general and also applies, e.g., for network-forming liquids like silica.

A single crystal with point defects also has a finite solidity length, but here the concept is not relevant because the crystal structure defines solid-like particle correlations over distances stretching to infinity. For an ultraviscous liquid, on the other hand, due to the lack of a lattice, rigid distance correlations apply only below the solidity length.

Furukawa has argued that the length ξ defined by $\xi^4 \equiv a^4\tau_\alpha/\tau_0$, in which τ_0 is a microscopic time, is the characteristic length over which long-lived stress is sustained.^{76,77} He proposed that an ultraviscous liquid may be regarded as an ordinary liquid composed of clusters of size $\xi \sim l_s$, and that hydrodynamics only applies on length scales above ξ . Much of the physics probed in experiments takes place *below* the solidity length, however, e.g., dielectric relaxation or NMR experiments probe a molecular average property. In fact, measuring a macroscopic dynamic property like the viscosity η is increasingly difficult as the glass transition is approached.⁷⁸

Conservation Laws. Below the solidity length, the laws of conservation of the number of particles, momentum, and energy play roles different from in ordinary liquids where these laws form the basis of hydrodynamics.^{6,28,35,79,80} Consider first particle conservation. A molecular dynamics simulation keeps track of the individual particles, but things look different in a coarse-grained description based on a continuous density field, $\rho(\mathbf{r}, t)$. This field is constant in time until it changes due to a flow event, a change that below the solidity length may be regarded as instantaneous. In general, flow events are not spherically symmetric, but this assumption can be made

initially when discussing the density change at the flow event center.

A spherically symmetric flow event leads as mentioned to purely radial displacements in the surroundings $\propto 1/r^2$.⁶⁵ The divergence of the displacement field, which determines the local density change, is zero (compare Gauss' law for the point-charge electric field $\propto 1/r^2$). On the other hand, this radial displacement can only take place if there is a density change at the flow-event center. Hence, if the density change after coarse-graining over a few molecular distances is denoted by $\Delta\rho(\mathbf{r})$, a flow event at \mathbf{r}_0 leads to

$$\Delta\rho(\mathbf{r}) = 0 \quad (5)$$

in its surroundings. Comparing the situation before and after the flow event, local particle conservation will appear to be violated because the density changes only at \mathbf{r}_0 . What happens is reminiscent of Hilbert's hotel, the full infinite hotel that hosts new arrivals by asking all guests to move to a room of one higher number.

Below the solidity length, flow events may as mentioned be regarded as instantaneous. This leads to a coarse-grained description with no visible trace of particle-number conservation,⁸¹

$$\dot{\rho}(\mathbf{r}, t) = \sum_j b_j \delta(\mathbf{r} - \mathbf{r}_j) \delta(t - t_j) \quad (6)$$

Here b_j is a dimensionless measure of the magnitude of the flow event at time t_j and position \mathbf{r}_j . Apparent density nonconservation holds also if one takes into account the minor density changes of the more realistic anisotropic Eshelby-type flow events discussed, e.g., in refs 62, 66, 67, and 82. In that case, the right-hand side of eq 6 acquires an additional "advective" term reflecting the long-range minor effects of flow events on the density, a term that also after coarse-graining conforms to density conservation.

Below the solidity length, mechanical equilibrium applies in the time between flow events, i.e., time-averaged forces are zero. In a coarse-grained description this is expressed as zero divergence of the stress tensor, $\sigma_{\mu\nu}(\mathbf{r}, t)$ ⁶⁵

$$\partial_\mu \sigma_{\mu\nu}(\mathbf{r}, t) = 0 \quad (7)$$

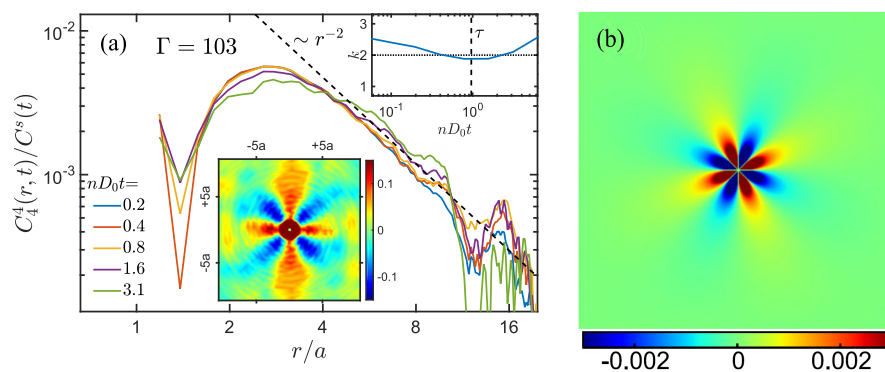


Figure 5. Spatial strain and stress correlations in ultraviscous liquids. (a) Experimental data for the strain correlations of a 2D colloidal glass-forming liquid. The lower inset shows the spatial correlation function of the xy strain-tensor change over a time $t \gg \tau_\alpha$ where green is zero. The curves are normalized spherical-harmonics projections of this function at different times, which are proportional to $1/r^2$ as predicted for Eshelby patterns in 2D.^{62,65,66,69,82} Reproduced from ref 63. Copyright 2016 American Physical Society. (b) Stress-tensor correlations in a 2d binary viscous liquid. The figure shows the correlations between the normal-shear-stress increment of a single flow event. Reproduced from ref 62. Copyright 2014 American Physical Society.

in which $\mathbf{r} = (x_1, x_2, x_3)$ and ∂_μ is the spatial derivative with respect to x_μ . In this approach, the dynamics is regarded as a series of instantaneous transitions between states of mechanical equilibrium, each of which conforms to eq 7.

Momentum conservation likewise plays little role in the dynamics below the solidity length. The situation is similar to that of point-defect motion in a crystal, for which one would not invoke momentum conservation to explain the physics. The same applies for energy conservation: in an ultraviscous liquid, energy flow predominantly takes place via heat conduction, just like in a solid, and this process is irrelevant for the rate of flow events or for explaining how these correlate in space and time. Note that we are not suggesting that strict particle, momentum, or energy conservation is violated, merely that these conservation laws are not relevant for understanding the physics of glass-forming liquids.^{8,83}

Flow Events in Plastic Flow of Glasses. The understanding of glass-forming liquids has benefitted greatly by learning from studies of forced flow of glasses. When a glass is subjected to a gradual shear deformation, it eventually yields by deforming irreversibly.^{84–88} The last 15 years has brought tremendous progress in the understanding of zero-temperature plastic flow of glasses,⁸⁹ which proceeds as a sequence of sudden, localized flow events.^{90–92} These generally do not take place at random locations, but at soft spots in the glass; compare Figure 4a.⁹³

Different methods have been suggested for identifying soft spots.⁸⁹ An early approach was to look for particles with a large finite-temperature vibrational mean-square displacement, a simple indicator that the potential is soft at the particle in question.⁹⁶ The mean local potential-energy fluctuation has also been used as a soft-spot identifier.⁹⁷ The local-yield-stress method^{94,98} considers a small sphere and constrains the outside system to deform affinely such that only the atoms inside the sphere can relax when the system is shear deformed. Different sphere locations and possible shear deformations are probed to identify the position of smallest local yield stress. This method works well for identifying the sites of plastic rearrangement but requires knowledge of the interaction potentials. Methods for identifying sites for plastic flow events based purely on structural information have also been devised^{99,100} using, e.g., a mean-field caging potential¹⁰¹ or machine-learning techniques.^{102,103} One such method¹⁰²

defines “softness” as a weighted integral over local radial pair-correlation functions and optimizes the weights for predicting sites of rearrangement by learning from plastic flows. The results obtained correlate well with those of the local-yield-stress method.^{102,103}

An alternative approach utilizes the fact that soft spots give rise to localized phonon modes, implying that the latter are good predictors for plasticity.^{104–108} Low-energy localized vibrational modes may be identified by a third-order expansion of the potential-energy function, a clever method that avoids the hybridization with the low-frequency sound-wave modes found by diagonalizing the Hessian.¹⁰⁹ Despite the above quoted strong indications of a connection between soft spots and relaxation sites, this link has exceptions and is not universally agreed upon.^{110–112}

To summarize, plastic flow takes place via sudden flow events. The physics is similar to what happens in an equilibrium ultraviscous liquid in which flow events are also usually located at “soft spots” (Figure 4b). A difference is that the time-sequence of flow events of a zero-temperature plastic flow is deterministic, while a glass-forming liquid’s flow events are stochastic. Another difference is the lack of isotropy of a plastic flow, which leads to preferred orientations of the Eshelby stress fields, to which we now turn.

Strain and Stress Correlations in the Liquid. We return below to the idea that flow events are controlled by the system’s elastic properties and focus here on another property of glasses, the fact that a flow event generally induces a quadrupolar stress-field change in the surroundings.¹¹³ This is explained by the 1957 theory of solid inclusions by Eshelby,⁶⁶ which applies also to disordered solids because these are effectively homogeneous on a long length scale. Eshelby calculated the long-range stress and strain changes of an inclusion by replacing it with localized forces in an elastic continuum. Each force gives rise to a momentum current into the solid, and since these forces must sum to zero, the result is a quadrupolar stress field.^{66,82}

An obvious question is whether the long-ranged stress correlations observed in glasses¹¹⁴ exist also in glass-forming liquids.^{112,115–117} One expects this to be the case below the solidity length because here the properties of the liquid’s inherent states—each of which corresponds to a $T = 0$ glass—is inherited by the equilibrium liquid (Figure 5).^{115,118–121}

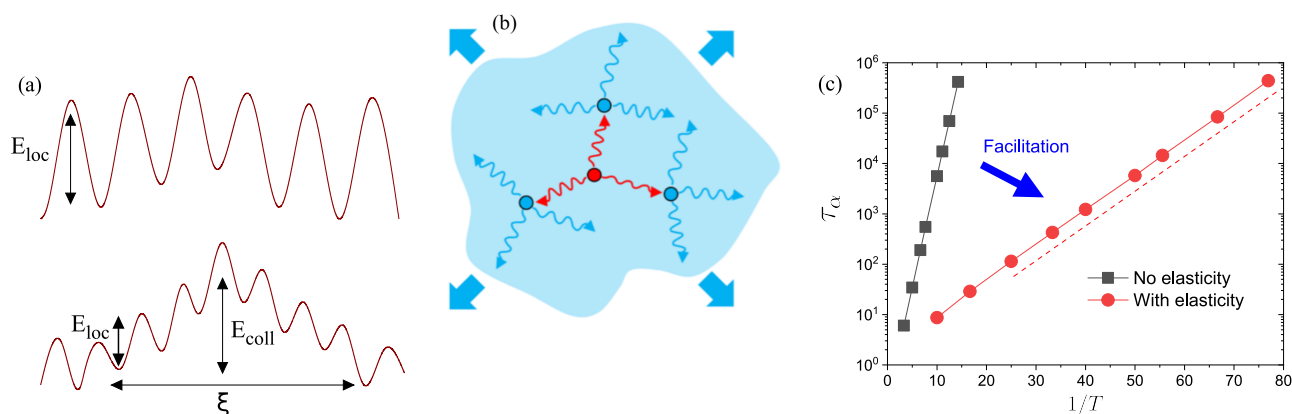


Figure 6. Elastic facilitation. (a) Two schematic free-energy landscapes in configuration space. The dynamics can be dominated by local energy barriers (upper panel) or by the growth of cooperative effects over some distance ξ (lower panel). Reproduced from ref 128. Copyright 2023 Authors, licensed under a Creative Commons License. (b) Avalanche of flow events induced by a single flow event that lowers some barriers in the surroundings, thereby catalyzing other flow events that induce yet others, etc. Reproduced from ref 134. Copyright 2023 Authors, licensed under a Creative Commons License. (c) Temperature dependence of τ_α in a simple model with and without elastic facilitation. Reproduced from ref 135. Copyright 2023 American Physical Society.

Lemaitre worked out the theory for the stress-tensor spatial autocorrelation function in a disordered isotropic solid. Remarkably, the $3 \times 3 \times 3 \times 3$ tensor $\langle \sigma_{\alpha\beta}(\mathbf{r}) \sigma_{\gamma\delta}(\mathbf{r}') \rangle$ is determined by just two functions of $|\mathbf{r} - \mathbf{r}'|$.^{62,69} In general, if X is the space or space-time coordinate and D_X is a linear differential operator of a field theory with equation of motion “ $D_X \phi(X) = \text{Noise}$ ”, one has $D_X \langle \phi(X) \phi(X') \rangle = 0$ whenever X' differs from X in all coordinates. Thus, according to the *solid-that-flows* picture, as a function of \mathbf{r}' the autocorrelation function $\langle \sigma_{\alpha\beta}(\mathbf{r}) \sigma_{\gamma\delta}(\mathbf{r}') \rangle$ obeys eq 7. In particular, it conforms to the Eshelby theory⁸² for $|\mathbf{r} - \mathbf{r}'| \rightarrow \infty$. The same applies to the more general space-time autocorrelation function $\langle \sigma_{\alpha\beta}(\mathbf{r}, t) \sigma_{\gamma\delta}(\mathbf{r}', t') \rangle$.

Long-ranged stress and strain correlations exist only below the solidity length, however. At longer length scales, the effects of one flow event are smeared out by those of others. Thus, beyond the solidity length l_s an exponential decay of the spatial stress autocorrelation function is to be expected. This means that in the liquid phase, the Lemaitre spatial autocorrelation functions⁶⁹ should be multiplied by a factor $\sim \exp(-|\mathbf{r} - \mathbf{r}'|/l_s)$.

We finally note that the nonzero stresses of an ultraviscous liquid modify nearby flow-event energy barriers. This is not taken into account in attempts to identify likely positions of flow events from specific structures,¹⁰⁰ which may explain why such attempts have only been moderately successful.¹²²

We end this Perspective by giving three examples of how the *solid-that-flows* picture elucidates experimental facts of glass-forming liquids.

Dynamic Heterogeneity and Elastic Facilitation. An important finding of the 1990s was that the dynamics of a glass-forming liquid is spatially inhomogeneous.^{38,39,123–125} At any given time, there are regions of considerable molecular motion and regions of little.^{23,126} This provides a simple explanation of the observed violation of the Stokes–Einstein relation between viscosity and diffusion coefficient:^{37,39,127} Fast particles take advantage of rapidly relaxing regions and contribute a great deal to D_{par} , but little to the overall structural relaxation rate quantified by τ_α via the viscosity.

What controls the temperature dependence of τ_α ? Figure 6a presents two fundamentally different scenarios.¹²⁸ In one case (upper panel), the local energy barrier controls the dynamics in the sense that it determines the overall relaxation rate. Alternatively, structural relaxation is a highly cooperative process that involves an entire sequence of flow events (lower panel). The latter scenario has been used to explain dynamic heterogeneities and is predicted, e.g., by the random first-order transition (RFOT) theory.^{75,129} RFOT is inspired by the theory of spin glasses, which are systems with no elastic interactions. In RFOT, the increase of the activation energy of τ_α upon cooling results from a correlation length ξ that grows due to the decrease of entropy.^{52,55} The fundamental RFOT prediction, which has been proven rigorously for infinite dimensions,¹³⁰ is that thermodynamics control the dynamics. This is challenged, however, by the fact that swap algorithms in finite dimensions^{131,132} can speed up computer simulations significantly without affecting the thermodynamics.^{74,133}

The local-barrier picture is the obvious one from the *solid-that-flows* view in which the situation is analogous to that of a plastic flow with flow events occurring at soft sites. That local barriers control the relaxation was demonstrated recently in simulations of a 3D polydisperse soft-repulsive-potential model.¹²⁸ By systematically identifying the flow events starting at a given inherent state, it was shown that upon cooling, the activation energy increases enough to account for the super-Arrhenius temperature dependence of τ_α . This means that, at least for the model in question, the dynamics is not cooperative; in particular, no divergence of the relaxation time is predicted at a finite temperature.^{131,136,137}

If τ_α is controlled by the individual flow-event activation energies, how does one explain dynamic heterogeneity? A promising candidate is facilitation, the idea that one flow event makes nearby flow events more likely.^{138–140} “Elastic facilitation” is a consequence of the fact that all flow events lead to long-range stress-tensor changes within the sphere defined by the solidity length. These lower the barriers of some potential nearby flow events and increase others.^{45,62,135,141} Because the exponential function is convex, the net effect is that one flow event makes neighboring flow events more likely.

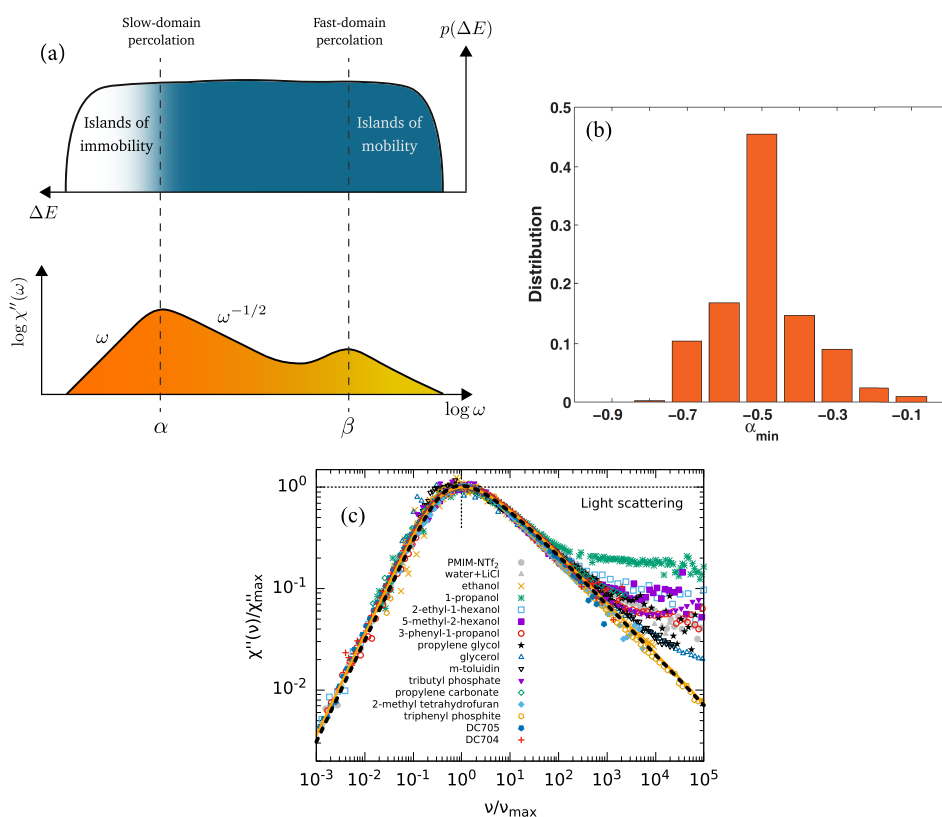


Figure 7. Linear-response consequences of the solidity of glass-forming liquids. (a) Double-percolation scenario for the frequency-dependent imaginary-part linear response, $\chi''(\omega)$, in the case of a very wide flow-event activation-energy distribution, $p(\Delta E)$. The distribution is constant in time, but the activation energy of any region changes over the τ_α time scale. The β relaxation is marked by the frequency corresponding to where the islands of mobility percolate; the α relaxation is where the islands of immobility percolate. The islands of immobility do not contribute to any relaxation because their barriers are too high and await being lowered by elastic facilitation and/or by “dissolving” the slow-domain percolation cluster defining the τ_α time scale. (b) Histogram of the minimum slopes above the α dielectric log–log loss peaks for 347 spectra of 53 glass-forming liquids. The prevalent minimum slopes are close to -0.5 . Reproduced from ref 182. Copyright 2009 Authors, licensed under a Creative Commons License. (c) Results from dynamic light scattering showing a $\chi''(\omega) \propto \omega^{-1/2}$ high-frequency decay for chemically quite different glass-forming liquids. The black dashed line is the imaginary part of $\chi(\omega) \propto 1/\sqrt{1+i\omega\tau_\alpha} + 1/(\sqrt{2} + \sqrt{1+i\omega\tau_\alpha})$, which can be derived from the density-dispersion relation $\Gamma(k) = \Gamma_0 + D_{\text{coh}}k^2$ that incorporates the apparent violation of density conservation via the Γ_0 term.¹⁹² Reproduced from ref 183. Copyright 2021 American Chemical Society.

Borrowing a term from NMR theory, this general mechanism has been referred to as “rate exchange”^{38,127,142}.

Elastic facilitation, which was first studied in glasses,^{62,143} is illustrated in Figure 6b. In a simple model,¹³⁵ this leads to a substantial reduction in the activation energy of τ_ω Figure 6c. In ref 134, it was proposed that an entire avalanche of flow events may be triggered by a single one, similar to what happens in plastic flow of glasses.^{88,144,145} Reference 146 considered a simple facilitated trap model⁵⁴ and showed that it results in an asymmetric α loss peak with an excess wing (see also refs 147 and 148).

Double-Percolation Scenario for Linear-Response Functions. Any linear-response property is quantified by a complex frequency-dependent response function, $\chi(\omega) = \chi'(\omega) + i\chi''(\omega)$. It is sometimes stated that a major mystery of glass-forming liquids is the observed broad loss peaks, $\chi''(\omega)$. Certainly, a Debye loss peak, $\chi''(\omega) \propto \omega\tau/[1 + (\omega\tau)^2]$ (which according to the fluctuation–dissipation theorem¹⁴⁹ corresponds to an exponential time-autocorrelation function) is rarely observed. But one could also argue that the loss peaks are, in fact, surprisingly narrow. In particular, in the vast majority of glass-forming liquids, dielectric, mechanical, and specific-heat loss peaks follow the Debye prediction on the

low-frequency side. This striking fact implies the existence of a quite sharp long-time cutoff in the relaxation-time distribution $p(\tau)$ defined by

$$\chi''(\omega) = \int_0^\infty \omega\tau/[1 + (\omega\tau)^2]p(\tau)d\tau$$

How can one understand this?

The disorder of a glass-forming liquid implies that flow-event energy barriers ΔE vary in space throughout the system at any given time. An *ad hoc* assumption is that at any given time, the barriers vary randomly in space according to some distribution. This is illustrated in the upper part of Figure 7a for the case of a distribution, $p(\Delta E)$, which is much wider than $k_B T$. The smallest barriers give rise to what Johari and Goldstein half a century ago termed “islands of mobility”¹⁵⁰ where fast, spatially isolated rearrangements take place. Such islands may involve just a few molecules or be larger, and they do not necessarily have a super well-defined contrast to the surroundings. On a longer time scale flow events involving larger barriers are gradually “activated”, and at some point they will percolate the structure. On that time scale, extended motion becomes possible within the rigid structure formed by the remaining system. In three dimensions, the percolation

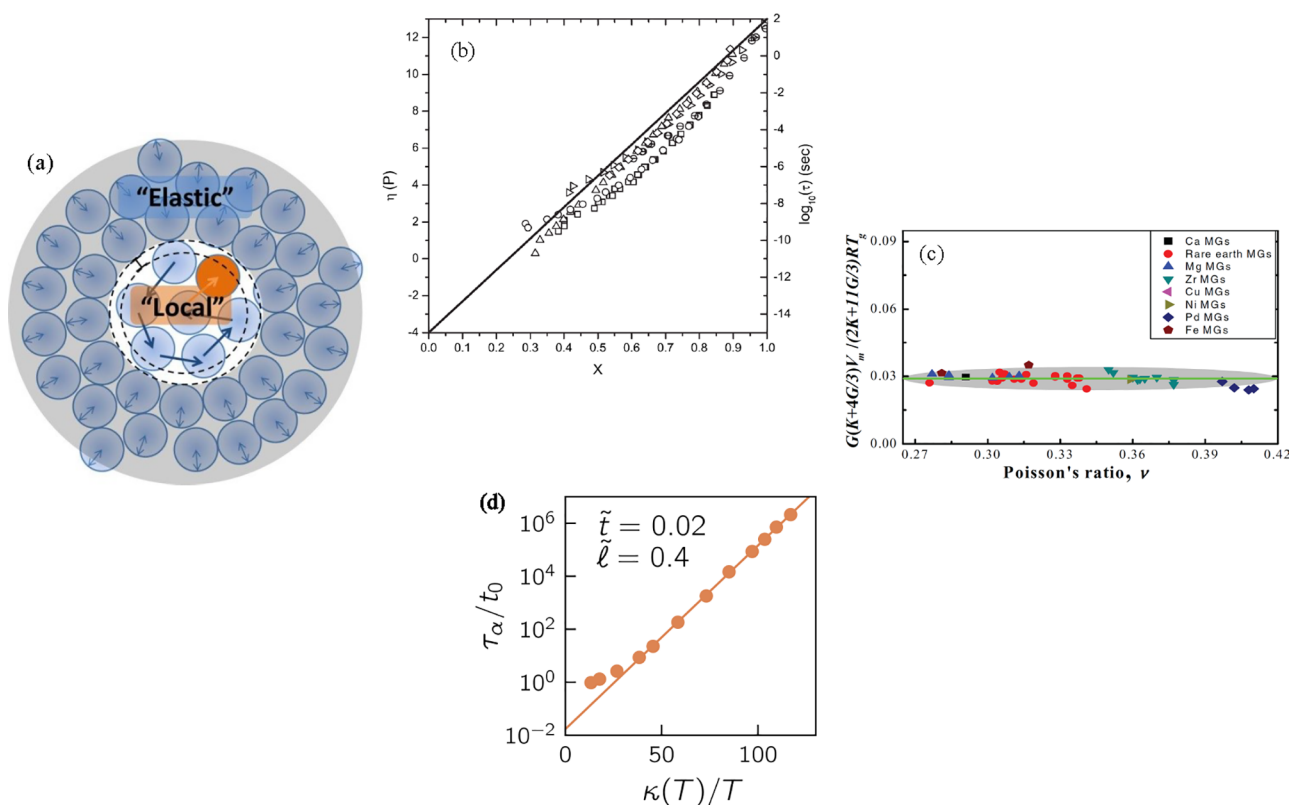


Figure 8. Elastic model predictions for the temperature dependence of τ_α . (a) Schematic picture of a flow event. The showing model for $\tau_\alpha(T)$ ignores the “local” contribution to the activation energy, which is small whenever interactions are strongly anharmonic.²¹² Reproduced from ref 213. Copyright 2013 American Chemical Society. (b) Logarithm of the viscosity of ten organic glass-forming liquids plotted as a function of $X \equiv G_\infty(T)T_g/(G_\infty(T_g)T)$. Equation 8 predicts a straight line ending at the limiting high-temperature viscosity (10^{-4} Pa·s = 10^{-5} Pa·s). Reproduced from ref 214. Copyright 2009 AIP Publishing. (c) Test of eq 9 for several metallic glasses in which G and K are the shear and bulk moduli of the glass and V_m is the molar volume. Reproduced from ref 206. Copyright 2012 Authors, licensed under a Creative Commons License. (d) For a binary Lennard-Jones model the activation energy of τ_α is proportional to the average microscopic dipole stiffness κ , i.e., $\log(\tau_\alpha/t_0) \propto \kappa(T)/T$ in which t_0 is phonon time. Reproduced from ref 211. Copyright 2021 AIP Publishing.

threshold is roughly one-quarter; in two dimensions, the threshold is 50% because a given set or its complement must percolate—and for geometric reasons, both cannot happen.^{151,152}

Consider next the largest barriers. Being also spatially isolated, these form “islands of immobility”. Including gradually smaller barriers, at some point there is slow-domain percolation. This defines a characteristic time scale that we identify with τ_α : on time scales shorter than τ_ω the system is rigid and can sustain an externally imposed shear stress, while on longer time scales the slow-domain percolation cluster “dissolves”, allowing the system to flow in response to an external stress.⁴ What happens then is that the system flows enough to loosen the structure around any high-energy-barrier location of the liquid. This lowers these barriers before they are transcended, which explains why loss peaks generally are Debye on the low-frequency side. This picture of the α relaxation may be referred to as “dynamic rigidity percolation”.¹⁵³ Note that the long-time flow does not mean the system is like a standard liquid at long times; it is still better regarded as a *solid-that-flows*.

A consequence of the above physical picture is that single-particle motion is predicted to be spatially heterogeneous on short time scales, but homogeneous on time scales longer than τ_α .^{125,154–157} That structural relaxation and thereby τ_α is controlled by the slow particles is an old idea,^{125,158–160} which

has recently been confirmed in experiments,¹⁶¹ as well as in equilibrium^{162,163} and aging¹⁵³ simulations.

The double-percolation picture translates as follows into a generic frequency-dependent loss, $\chi''(\omega)$. The largest barriers are as mentioned never overcome so the corresponding long relaxation times do not contribute to the loss. Consequently, $p(\tau)$ has a long-time cutoff roughly at τ_α and $\chi''(\omega)$ is Debye-like at low frequencies: $\chi''(\omega) \propto \omega$ whenever $\omega\tau_\alpha \ll 1$.¹⁶³ On shorter time scales, i.e., above the α loss-peak frequency $\sim 1/\tau_\omega$ solidity comes into effect, resulting in an asymmetric loss peak.¹⁶² Here we predict $\chi''(\omega) \propto \omega^{-1/2}$ based on solving a simple field theory for the density fluctuations in the Gaussian approximation, assuming a wavevector-dependent density decay rate of the form $\Gamma(k) = \Gamma_0 + D_{\text{coh}}k^2$ in which $\Gamma_0 \sim 1/\tau_\alpha \ll D_{\text{coh}}/a^2$.^{8,81} Conservation laws generally imply a $\Gamma(k) \propto k^2$ dispersion relation arising from the spatial Fourier transform of the ∇^2 operator of the diffusion equation,^{28,79} while the Γ_0 term corresponds to the apparent violation of density conservation discussed above.⁸¹ Note that Figure 7a relates to the case of a very wide $p(\Delta E)$, which for many equilibrium ultraviscous liquids may apply only at temperatures so low that the system cannot be equilibrated even in long-time experiments.

A second loss peak is expected at the frequency corresponding to fast-domain percolation (Figure 7a). Following Gao et al.¹⁶⁴ we identify this with the ubiquitous

Johari–Goldstein (JG) β process,¹⁵⁰ thereby taking several previous works to their logical consequence.^{165–176}

A double-percolation picture of glass-forming liquids was proposed already in 1996 by Novikov et al., who discussed percolation of liquid-like and solid-like domains defined by the largest and the smallest vibrational mean-square displacement, respectively.¹⁷⁷ A graphic description refers to the slow-domain percolation cluster as a “sponge” through which fast motion is possible.¹⁷⁸

While we have here focused on linear-response properties of equilibrium glass-forming liquids, it has been demonstrated in colloidal-glass experiments that percolation also controls glass plastic flow; thus, growing clusters of nonaffine deformation percolate at yielding.¹⁷⁹

The experimental situation is much less clear than the schematic picture in Figure 7a. In fact, there are only a few data for JG β relaxation in the equilibrium liquid phase. This is because above T_g the α and β processes usually interfere, often to the extent that the high-frequency α decay hides the β process that is reduced to an excess wing of the α process.^{162,180,181}

Turning to the α process, an analysis of dielectric spectra of 53 liquids at different temperatures revealed that the α high-frequency approximate exponent—identified as the minimum slope in a log–log plot of the loss, α_{\min} —is predominantly close to -0.5 (Figure 7b); α_{\min} moreover approaches -0.5 as $T \rightarrow T_g$.¹⁸² Recent light-scattering data confirm this picture,^{183,184} compare Figure 7c. We also note that recent extensive computer simulations find the exponent -0.38 ,¹⁶³ which is not far from -0.5 .

Elastic Models for the Temperature Dependence of τ_α . Point defects in simple crystals are either vacancies or interstitials.^{70,185} Such defects can jump, and the activation energy for a jump scales with the crystal's elastic constants.¹⁸⁶ In the *solid-that-flows* picture it is obvious to assume that the flow-event activation energy likewise is proportional to the elastic constants, here those that characterize fast deformations, i.e., the high-frequency plateau shear and bulk moduli. This idea defines the elastic models that exist in several versions,^{9,187} and which have been linked to models based on the decrease of free volume or increase of collective motion upon cooling.^{157,188} Note that in some models elasticity accounts for only part of the activation energy.^{189–191}

The simplest mean-field approach assumes that all flow-event activation energies scale in proportion to the macroscopic moduli. For a perfectly spherical flow event in a homogeneous solid, the surroundings experience, as mentioned, a radial displacement $\propto 1/r^2$. This results in a pure shear deformation, i.e., one with no density change except at the flow event center. Thus, the relevant elastic constant is the high-frequency plateau shear modulus G_∞ . The shoving model ignores the flow-event-center contribution to the activation energy and predicts¹⁹³

$$\tau_\alpha = \tau_0 e^{G_\infty(T)V_c/k_B T} \quad (8)$$

Here $\tau_0 \sim 10^{-13}$ s is a prefactor set by the phonon time scale and V_c is a microscopic volume. G_∞ of a glass-forming liquid is usually much more temperature dependent than in the corresponding crystal; in fact $G_\infty(T)$ often increases enough upon cooling to account for the non-Arrhenius $\tau_\alpha(T)$. The physical picture of the shoving model is shown in Figure 8a. Although many data conform to eq 8,¹⁹¹ compare Figure 8b,

the shoving model does not apply for all glass-forming liquids.^{191,194}

In so far as the dominant contribution to the activation energy derives from displacements around the flow event, not at its center, G_∞ controls more than 90% of the activation energy.¹⁹⁵ Elastic models emphasizing instead the bulk modulus also exist, however.^{191,196} A popular elastic model expression is $\log(\tau_\alpha) \propto 1/\langle u^2 \rangle$ in which $\langle u^2 \rangle$ is the vibrational mean-square displacement.^{9,191,197–200} In this approach T_g is characterized by a definite value of $1/\langle u^2 \rangle$, giving rise to a glass analogue of the famous Lindemann melting criterion.^{201–203} This prediction has been investigated by assuming V_c is a system-independent fraction of the molar volume V_m and that all vibrations are phonons controlled by G_∞ and the high-frequency plateau bulk modulus, K_∞ . At the glass transition, these moduli freeze into their glass values, G and K . A straightforward calculation based on the existence of two transverse and one longitudinal phonon for each wavevector leads^{204–206} to

$$T_g \propto GV_m \frac{K + 4G/3}{2K + 11G/3} \quad (9)$$

with a universal constant of proportionality. This is validated for several bulk metallic glasses in Figure 8c, thus making it possible to predict T_g from glass properties.²⁰⁷

The above approaches either assume that the elastic properties are constant throughout the sample or that the local elastic constants^{208,209} scale proportionally when temperature is changed.²¹⁰ Kapteijns et al. studied the energy landscape of a binary Lennard-Jones model to investigate the influence of the elastic constants between neighboring particles on the temperature dependence of τ_α .²¹¹ The activation energy of τ_α was found to be proportional to the average “stiffness” between neighboring particles of the liquid's inherent structures. This leads to the straight-line prediction of Figure 8d and suggests an alternative microscopic explanation of why elastic models account for many non-Arrhenius data.¹⁹⁴

DISCUSSION

This perspective has reviewed arguments that a glass-forming liquid below the solidity length is more like a *solid-that-flows* than like ordinary liquids. The focus has been on the dynamics, leaving out a discussion of thermodynamic properties and their correlation to the dynamics.^{18,52} In regard to experimental predictions, we note that the double-percolation picture does not apply in 2D. That is, if α and β relaxations as suggested derive from slow- and fast-domain percolation, respectively, no separate Johari–Goldstein β processes should exist in 2D because the percolation threshold is here 50%. It has been argued from simulations that the glass transition in 2D indeed is different from in 3D in several respects.^{131,215,216} Another prediction is that all molecules contribute to the β relaxation in the liquid phase, albeit only a fraction of them at any given time, while in the glass some molecules contribute and many do not.^{163,217}

What is the difference between the *solid-that-flows* picture and the standard Maxwell model in which a liquid behaves as a solid over short times? One difference is the existence of a solidity length in the *solid-that-flows* view, a consequence of the fact that the sound velocity is finite, quantifying the length scale above which the picture breaks down. Another difference is that, whereas the Maxwell model predicts standard liquid

behavior at long times, the solid-like behavior below the solidity length persists. One consequence of this is the apparent density nonconservation in coarse-grained descriptions.


Not everything discussed in this paper can be correct for the simple reason that there are several inconsistencies. We end the paper by listing these and other issues in order to illustrate that there is still no self-contained picture of glass-forming liquids' solidity and its consequences:

- The derivation of the solidity length eq 4 assumes that each place in the liquid on average gives rise to one flow event every τ_α . This is inconsistent with the double-percolation picture of Figure 7a in which a wide range of activation energies is involved. This inconsistency persists even after taking into account that the islands of immobility are “renormalized” by facilitation or otherwise and lowered to the slow-domain percolation activation energy defining τ_α . This dilemma may be resolved by following Furukawa and instead define l_s as the length scale beyond which ordinary hydrodynamics applies;⁷⁶ as noted above this leads to virtually the same expression as eq 4. While $l_s \propto \tau_\alpha^{1/4}$ has recently been confirmed in connection with nonlinear flow modeling,²¹⁸ it should be mentioned that other recent works predict $l_s \propto \tau_\alpha^{1/2219}$ and $l_s \propto \tau_\alpha^{1/3,5}$, a matter that needs to be resolved. How to determine l_s in experiments is another important challenge for future work.²¹⁸
- It is not obvious that elastic facilitation (Figure 6b and c) is enough to eradicate the largest quarter of the barriers (Figure 7a). After all, the stress changes induced by one flow event decay in space as $\propto 1/r^3$, which is rather rapid, so other facilitation mechanisms may be needed.^{163,220} We favor the above-mentioned possibility that the entire system flows slightly on time scales longer than τ_α implying that all stresses decorrelate, including those that keep in place the solid structure defining the local energy barriers.
- Based on the double-percolation picture one would expect an experimental signature of the percolation critical exponents.^{162,221} This contradicts the prediction that $\chi''(\omega) \propto \omega^{-1/2}$ above the α loss peak frequency. Moreover, it was recently shown that the (zero-parameter) random-barrier model²²² provides an excellent fit to the inherent mean-square displacement as a function of time for a binary deeply supercooled Lennard-Jones liquid.²²³ It is difficult to reconcile that with the prediction for the α high-frequency loss, $\chi''(\omega) \propto \omega^{-1/2}$.²²⁴
- The shoving model assumes uniform elasticity on the short time scale, i.e., does not take into account dynamic heterogeneities. If all flow-event barriers scale proportionally when temperature is changed, this temperature scaling is inherited by $G_\infty(T)$.²¹⁰ Even under this assumption, however, one would not expect the flow-event sequences to be temperature invariant because sequences avoiding large barriers become increasingly important as the temperature is lowered. This should lead to a modification of eq 8.

Clearly, much further work is needed before the *solid-that-flows* picture has matured into a simple and coherent one.

AUTHOR INFORMATION

Author

Jeppe C. Dyre – “Glass and Time”, IMFUFA, Dept. of Sciences, Roskilde University, DK-4000 Roskilde, Denmark;
 orcid.org/0000-0002-0770-5690

Complete contact information is available at:
<https://pubs.acs.org/10.1021/acs.jpcllett.3c03308>

Notes

The author declares no competing financial interest.

Biography



Jeppe C. Dyre is professor of physics at Roskilde University and a member of the Royal Danish Academy of Sciences and Letters. After studying mathematics and physics at the University of Copenhagen, he has been with Roskilde University since 1984, where he received his Ph.D. in theoretical physics. Originally interested in solid-state diffusion, ac electrical conduction in disordered solids, and nonlinear response theory and rheology, he has for many years worked on the physics of highly viscous liquids and the glass transition. Currently, he is a VILLUM investigator with a focus on isomorph theory.

ACKNOWLEDGMENTS

The author gratefully thanks the following colleagues for suggestions improving the presentation: Akira Furukawa, Anael Lemaitre, Giulio Biroli, Jack Douglas, Jesper Hansen, Ken Schweizer, Lorenzo Costigliola, Mark Ediger, Massimo Pica Ciamarra, Matthias Fuchs, Misaki Ozawa, Nick Bailey, Peter Harrowell, Roland Böhmer, Thomas Schröder, and Walter Kob. Solvej Knudsen and Heine Larsen are thanked for technical assistance. This work was supported by the VILLUM Foundation's *Matter* grant VIL16515.

REFERENCES

- (1) Lebowitz, J. L. Statistical mechanics – A review of selected rigorous results. *Annu. Rev. Phys. Chem.* **1968**, *19*, 389.
- (2) Sausset, F.; Biroli, G.; Kurchan, J. Do solids flow? *J. Stat. Phys.* **2010**, *140*, 718.
- (3) Saw, S.; Harrowell, P. Rigidity in condensed matter and its origin in configurational constraint. *Phys. Rev. Lett.* **2016**, *116*, No. 137801.
- (4) Tong, H.; Sengupta, S.; Tanaka, H. Emergent solidity of amorphous materials as a consequence of mechanical self-organisation. *Nat. Commun.* **2020**, *11*, 4863.
- (5) Furukawa, A. Transverse viscous transport in classical solid states. *Phys. Rev. Lett.* **2021**, *127*, No. 245901.
- (6) Baggioni, M.; Landry, M.; Zaccane, A. Deformations, relaxation, and broken symmetries in liquids, solids, and glasses: A unified topological field theory. *Phys. Rev. E* **2022**, *105*, No. 024602.

- (7) Tu, C.-H.; Steinhart, M.; Berger, R.; Kappl, M.; Butt, H.-J.; Floudas, G. When crystals flow. *Sci. Adv.* **2023**, *9*, No. eadg8865.
- (8) Dyre, J. C. Ten themes of viscous liquid dynamics. *J. Phys.: Condens. Matter* **2007**, *19*, No. 205105.
- (9) Dyre, J. C. The glass transition and elastic models of glass-forming liquids. *Rev. Mod. Phys.* **2006**, *78*, 953.
- (10) Johari, G. P. Introduction to the glassy state in the undergraduate curriculum. *J. Chem. Educ.* **1974**, *51*, 23.
- (11) Angell, C. A. Formation of glasses from liquids and biopolymers. *Science* **1995**, *267*, 1924.
- (12) Debenedetti, P. G.; Stillinger, F. H. Supercooled liquids and the glass transition. *Nature* **2001**, *410*, 259.
- (13) Alba-Simionesco, C.; Tarjus, G. A perspective on the fragility of glass-forming liquids. *J. Non-Cryst. Solids X* **2022**, *14*, No. 100100.
- (14) Harrison, G. *The Dynamic Properties of Supercooled Liquids*; Academic Press: New York, 1976.
- (15) Brawer, S. *Relaxation in Viscous Liquids and Glasses*; American Ceramic Society: Columbus, OH, 1985.
- (16) Varshneya, A. K. *Fundamentals of Inorganic Glasses*; Academic Press: New York, 1994.
- (17) Ediger, M. D.; Angell, C. A.; Nagel, S. R. Supercooled liquids and glasses. *J. Phys. Chem.* **1996**, *100*, No. 13200.
- (18) Angell, C. A.; Ngai, K. L.; McKenna, G. B.; McMillan, P. F.; Martin, S. W. Relaxation in glass-forming liquids and amorphous solids. *J. Appl. Phys.* **2000**, *88*, 3113.
- (19) Berthier, L.; Biroli, G. Theoretical perspective on the glass transition and amorphous materials. *Rev. Mod. Phys.* **2011**, *83*, 587.
- (20) Hunter, G. L.; Weeks, E. R. The physics of the colloidal glass transition. *Rep. Prog. Phys.* **2012**, *75*, No. 066501.
- (21) Wang, W. H. The elastic properties, elastic models and elastic perspectives of metallic glasses. *Prog. Mater. Sci.* **2012**, *57*, 487.
- (22) McKenna, G. B.; Simon, S. L. 50th anniversary perspective: Challenges in the dynamics and kinetics of glass-forming polymers. *Macromolecules* **2017**, *50*, 6333.
- (23) Tanaka, H.; Tong, H.; Shi, R.; Russo, J. Revealing key structural features hidden in liquids and glasses. *Nat. Rev. Phys.* **2019**, *1*, 333.
- (24) Mauro, J. C. *Materials Kinetics: Transport and Rate Phenomena*; Elsevier: Amsterdam, Netherlands, 2021.
- (25) Alba-Simionesco, C. Organic glass-forming liquids and the concept of fragility. *C. R. Phys.* **2023**, *24*, 1.
- (26) Mooney, M. A theory of the viscosity of a Maxwellian elastic liquid. *Trans. Soc. Rheol.* **1957**, *1*, 63.
- (27) Lamb, J. Viscoelasticity and lubrication: A review of liquid properties. *J. Rheol.* **1978**, *22*, 317.
- (28) Hansen, J.-P.; McDonald, I. R. *Theory of Simple Liquids: With Applications to Soft Matter*, 4th ed.; Academic Press: New York, 2013.
- (29) Barrat, J.-L.; Hansen, J.-P. *Basic Concepts for Simple and Complex Liquids*; Cambridge University Press, 2003.
- (30) Bacher, A. K.; Schröder, T. B.; Dyre, J. C. Explaining why simple liquids are quasi-universal. *Nat. Commun.* **2014**, *5*, 5424.
- (31) Dyre, J. C. Simple liquids' quasiuniversality and the hard-sphere paradigm. *J. Phys.: Condens. Matter* **2016**, *28*, No. 323001.
- (32) Bacher, A. K.; Schröder, T. B.; Dyre, J. C. The EXP pair-potential system. I. Fluid phase isotherms, isochores, and quasiuniversality. *J. Chem. Phys.* **2018**, *149*, No. 114501.
- (33) Landau, L. D.; Lifshitz, E. M. *Fluid Mechanics*; Pergamon: Oxford, 1959.
- (34) Costigliola, L.; Heyes, D. M.; Schröder, T. B.; Dyre, J. C. Revisiting the Stokes-Einstein relation without a hydrodynamic diameter. *J. Chem. Phys.* **2019**, *150*, No. 021101.
- (35) Hansen, J. S. *Nanoscale Hydrodynamics of Simple Systems* Cambridge University Press, 2022.
- (36) Fajara, F.; Geil, B.; Sillescu, H.; Fleischer, G. Translational and rotational diffusion in supercooled orthoterphenyl close to the glass transition. *Z. Phys. B – Cond. Mater.* **1992**, *88*, 195.
- (37) Tarjus, G.; Kivelson, D. Breakdown of the Stokes-Einstein relation in supercooled liquids. *J. Chem. Phys.* **1995**, *103*, 3071.
- (38) Sillescu, H. Heterogeneity at the glass transition: a review. *J. Non-Cryst. Solids* **1999**, *243*, 81.
- (39) Ediger, M. D. Spatially heterogeneous dynamics in supercooled liquids. *Annu. Rev. Phys. Chem.* **2000**, *51*, 99.
- (40) Swallen, S. F.; Bonvallet, P. A.; McMahon, R. J.; Ediger, M. D. Self-diffusion of *tris*-naphthylbenzene near the glass transition temperature. *Phys. Rev. Lett.* **2003**, *90*, No. 015901.
- (41) Harris, K. R. The fractional Stokes-Einstein equation: Application to Lennard-Jones, molecular, and ionic liquids. *J. Chem. Phys.* **2009**, *131*, No. 054503.
- (42) Mallamace, F.; Branca, C.; Corsaro, C.; Leone, N.; Sporeen, J.; Chen, S.-H.; Stanley, H. E. Transport properties of glass-forming liquids suggest that dynamic crossover temperature is as important as the glass transition temperature. *Proc. Natl. Acad. Sci. U.S.A.* **2010**, *107*, No. 22457.
- (43) Poling, B. E.; Prausnitz, J. M.; O'Connell, J. P. *The properties of Gases and Liquids*, 5th ed.; McGraw-Hill: New York, 2001.
- (44) Khrapak, S. Bridgman formula for the thermal conductivity of atomic and molecular liquids. *J. Mol. Liq.* **2023**, *381*, No. 121786.
- (45) Chacko, R. N.; Landes, F. P.; Biroli, G.; Dauchot, O.; Liu, A. J.; Reichman, D. R. Elastoplasticity mediates dynamical heterogeneity below the mode coupling temperature. *Phys. Rev. Lett.* **2021**, *127*, No. 048002.
- (46) Dyre, J. C. Solidity of viscous liquids. *Phys. Rev. E* **1999**, *59*, 2458.
- (47) Schröder, T. B.; Sastry, S.; Dyre, J. C.; Glotzer, S. C. Crossover to potential energy landscape dominated dynamics in a model glass-forming liquid. *J. Chem. Phys.* **2000**, *112*, 9834.
- (48) Stoppelman, J. P.; McDaniel, J. G.; Cicerone, M. T. Excitations follow (or lead?) density scaling in propylene carbonate. *J. Chem. Phys.* **2022**, *157*, No. 204506.
- (49) Wang, W. H. Dynamic relaxations and relaxation-property relationships in metallic glasses. *Prog. Mater. Sci.* **2019**, *106*, No. 100561.
- (50) Widmer-Cooper, A.; Harrowell, P. Central role of thermal collective strain in the relaxation of structure in a supercooled liquid. *Phys. Rev. E* **2009**, *80*, No. 061501.
- (51) Kauzmann, W. The nature of the glassy state and the behavior of liquids at low temperatures. *Chem. Rev.* **1948**, *43*, 219.
- (52) Adam, G.; Gibbs, J. H. On temperature dependence of cooperative relaxation properties in glass-forming liquids. *J. Chem. Phys.* **1965**, *43*, 139.
- (53) Goldstein, M. Glass and other relaxations in liquids, Faraday Symp. Chem. Soc. **1972**, *6*, 7.
- (54) Dyre, J. C. Master-equation approach to the glass transition. *Phys. Rev. Lett.* **1987**, *58*, 792.
- (55) Lubchenko, V.; Wolynes, P. G. Theory of Structural Glasses and Supercooled Liquids. *Annu. Rev. Phys. Chem.* **2007**, *58*, 235.
- (56) Mirigian, S.; Schweizer, K. S. Elastically cooperative activated barrier hopping theory of relaxation in viscous fluids. II. Thermal liquids. *J. Chem. Phys.* **2014**, *140*, No. 194507.
- (57) Wang, Z.; Wang, W.-H. Flow units as dynamic defects in metallic glassy materials. *Natl. Sci. Rev.* **2019**, *6*, 304.
- (58) Goldstein, M. Viscous liquids and the glass transition: A potential energy barrier picture. *J. Chem. Phys.* **1969**, *51*, 3728.
- (59) Stillinger, F. H. A topographic view of supercooled liquids and glass formation. *Science* **1995**, *267*, 1935.
- (60) Doliwa, B.; Heuer, A. What does the potential energy landscape tell us about the dynamics of supercooled liquids and glasses? *Phys. Rev. Lett.* **2003**, *91*, No. 235501.
- (61) Chattoraj, J.; Lemaitre, A. Elastic signature of flow events in supercooled liquids under shear. *Phys. Rev. Lett.* **2013**, *111*, No. 066001.
- (62) Lemaitre, A. Structural relaxation is a scale-free process. *Phys. Rev. Lett.* **2014**, *113*, No. 245702.
- (63) Illing, B.; Fritschi, S.; Hajnal, D.; Klux, C.; Keim, P.; Fuchs, M. Strain pattern in supercooled liquids. *Phys. Rev. Lett.* **2016**, *117*, No. 208002.
- (64) Böhmer, R.; Hinze, G. Reorientations in supercooled glycerol studied by two-dimensional time-domain deuteron nuclear magnetic resonance spectroscopy. *J. Chem. Phys.* **1998**, *109*, 241.

- (65) Landau, L. D.; Lifshitz, E. M. *Theory of Elasticity*; Pergamon: Oxford, 1959.
- (66) Eshelby, J. D. The determination of the elastic field of an ellipsoidal inclusion, and related problems. *Proc. R. Soc. (London)* **1957**, *241*, 376.
- (67) Dyre, J. C. Solidity of viscous liquids. II. Anisotropic flow events. *Phys. Rev. E* **1999**, *59*, 7243.
- (68) Lemaitre, A. Tensorial analysis of Eshelby stresses in 3D supercooled liquids. *J. Chem. Phys.* **2015**, *143*, No. 164515.
- (69) Lemaitre, A. Stress correlations in glasses. *J. Chem. Phys.* **2018**, *149*, No. 104107.
- (70) Ashcroft, N. W.; Mermin, N. D. *Solid State Physics*; Holt, Rinehart and Winston, 1976.
- (71) Weingartner, N. B.; Nussinov, Z. Probing local structure in glass by the application of shear. *J. Stat. Mech.: Theory Exp.* **2016**, *2016*, No. 094001.
- (72) Berthier, L.; Biroli, G.; Bouchaud, J.-P.; Cipelletti, L.; van Saarloos, W., Eds., *Dynamical Heterogeneities in Glasses, Colloids, and Granular Media*; Oxford Univ. Press, 2011.
- (73) Karmakar, S.; Dasgupta, C.; Sastry, S. Growing length scales and their relation to timescales in glass-forming liquids. *Annu. Rev. Cond. Mater. Phys.* **2014**, *5*, 255.
- (74) Wyart, M.; Cates, M. E. Does a growing static length scale control the glass transition? *Phys. Rev. Lett.* **2017**, *119*, No. 195501.
- (75) Biroli, G.; Bouchaud, J. P. The RFOT theory of glasses: Recent progress and open issues. *C. R. Phys.* **2023**, *24*, 1.
- (76) Furukawa, A. Simple picture of supercooled liquid dynamics: Dynamic scaling and phenomenology based on clusters. *Phys. Rev. E* **2013**, *87*, No. 062321.
- (77) Furukawa, A. The emergence of cooperativity accompanying vitrification: insights from density fluctuation dynamics. *J. Stat. Mech.* **2019**, *2019*, No. 084001.
- (78) Hecksher, T.; Olsen, N. B.; Nelson, K. A.; Dyre, J. C.; Christensen, T. Mechanical spectra of glass-forming liquids. I. Low-frequency bulk and shear moduli of DC704 and 5-PPE measured by piezoceramic transducers. *J. Chem. Phys.* **2013**, *138*, 12A543.
- (79) Kadanoff, L. P.; Martin, P. C. Hydrodynamic equations and correlation functions. *Ann. Phys.* **1963**, *24*, 419.
- (80) Martin, P. C.; Parodi, O.; Pershan, P. S. Unified hydrodynamic theory for crystals, liquid crystals, and normal fluids. *Phys. Rev. A* **1972**, *6*, 2401.
- (81) Dyre, J. C. Solidity of viscous liquids. IV. Density fluctuations. *Phys. Rev. E* **2006**, *74*, No. 021502.
- (82) Eshelby, J. D. The elastic field outside an ellipsoidal inclusion. *Proc. R. Soc. (London)* **1959**, *252*, 561.
- (83) Dyre, J. C. Violations of conservation laws in viscous liquid dynamics. *Philos. Mag.* **2007**, *87*, 497.
- (84) Schall, P.; Weitz, D. A.; Spaepen, F. Structural rearrangements that govern flow in colloidal glasses. *Science* **2007**, *318*, 1895.
- (85) Lin, J.; Lerner, E.; Rosso, A.; Wyart, M. Scaling description of the yielding transition in soft amorphous solids at zero temperature. *Proc. Natl. Acad. Sci. U.S.A.* **2014**, *111*, No. 14382.
- (86) Voigtmann, T. Nonlinear glassy rheology. *Curr. Opin. Colloid Interface Sci.* **2014**, *19*, 549.
- (87) Hufnagel, T. C.; Schuh, C. A.; Falk, M. L. Deformation of metallic glasses: Recent developments in theory, simulations, and experiments. *Acta Mater.* **2016**, *109*, 375.
- (88) Nicolas, A.; Ferrero, E. E.; Martens, K.; Barrat, J.-L. Deformation and flow of amorphous solids: Insights from elastoplastic models. *Rev. Mod. Phys.* **2018**, *90*, No. 045006.
- (89) Richard, D.; Ozawa, M.; Patinet, S.; Stanifer, E.; Shang, B.; Ridout, S. A.; Xu, B.; Zhang, G.; Morse, P. K.; Barrat, J.-L.; Berthier, L.; Falk, M. L.; Guan, P.; Liu, A. J.; Martens, K.; Sastry, S.; Vandembroucq, D.; Lerner, E.; Manning, M. L. Predicting plasticity in disordered solids from structural indicators. *Phys. Rev. Mater.* **2020**, *4*, No. 113609.
- (90) Falk, M. L.; Langer, J. S. Dynamics of viscoplastic deformation in amorphous solids. *Phys. Rev. E* **1998**, *57*, 7192.
- (91) Tanguy, A.; Leonforte, F.; Barrat, J.-L. Plastic response of a 2D Lennard-Jones amorphous solid: Detailed analysis of the local rearrangements at very slow strain rate. *Eur. Phys. J. E* **2006**, *20*, 355.
- (92) Bouchbinder, E.; Langer, J. S.; Procaccia, I. Athermal shear-transformation-zone theory of amorphous plastic deformation. I. Basic principles. *Phys. Rev. E* **2007**, *75*, No. 036107.
- (93) Lerner, E. Micromechanics of nonlinear plastic modes. *Phys. Rev. E* **2016**, *93*, No. 053004.
- (94) Barbot, A.; Lerbinger, M.; Hernandez-Garcia, A.; Garcia-Garcia, R.; Falk, M. L.; Vandembroucq, D.; Patinet, S. Local yield stress statistics in model amorphous solids. *Phys. Rev. E* **2018**, *97*, No. 033001.
- (95) Lerbinger, M.; Barbot, A.; Vandembroucq, D.; Patinet, S. Relevance of shear transformations in the relaxation of supercooled liquids. *Phys. Rev. Lett.* **2022**, *129*, No. 195501.
- (96) Widmer-Cooper, A.; Harrowell, P. Predicting the long-time dynamic heterogeneity in a supercooled liquid on the basis of short-time heterogeneities. *Phys. Rev. Lett.* **2006**, *96*, No. 185701.
- (97) Zylberg, J.; Lerner, E.; Bar-Sinai, Y.; Bouchbinder, E. Local thermal energy as a structural indicator in glasses. *Proc. Natl. Acad. Sci. U.S.A.* **2017**, *114*, 7289.
- (98) Patinet, S.; Vandembroucq, D.; Falk, M. L. Connecting local yield stresses with plastic activity in amorphous solids. *Phys. Rev. Lett.* **2016**, *117*, No. 045501.
- (99) Coslovich, D. Locally preferred structures and many-body static correlations in viscous liquids. *Phys. Rev. E* **2011**, *83*, No. 051505.
- (100) Royall, C. P.; Williams, S. R. The role of local structure in dynamical arrest. *Phys. Rep.* **2015**, *560*, 1.
- (101) Nandi, M. K.; Bhattacharyya, S. M. Microscopic theory of softness in supercooled liquids. *Phys. Rev. Lett.* **2021**, *126*, No. 208001.
- (102) Cubuk, E. D.; Ivancic, R. J. S.; Schoenholz, S. S.; Strickland, D. J.; Basu, A.; Davidson, Z. S.; Fontaine, J.; Hor, J. L.; Huang, Y.-R.; Jiang, Y.; Keim, N. C.; Koshigan, K. D.; Lefever, J. A.; Liu, T.; Ma, X.-G.; Magagnoli, D. J.; Morrow, E.; Ortiz, C. P.; Rieser, J. M.; Shavit, A.; Still, T.; Xu, Y.; Zhang, Y.; Nordstrom, K. N.; Arratia, P. E.; Carpick, R. W.; Durian, D. J.; Fakhraei, Z.; Jerolmack, D. J.; Lee, D.; Li, J.; Riggelman, R.; Turner, K. T.; Yodh, A. G.; Gianola, D. S.; Liu, A. J. Structure-property relationships from universal signatures of plasticity in disordered solids. *Science* **2017**, *358*, 1033.
- (103) Boattini, E.; Marin-Aguilar, S.; Mitra, S.; Foffi, G.; Smalenburg, F.; Filion, L. Autonomously revealing hidden local structures in supercooled liquids. *Nat. Commun.* **2020**, *11*, 5479.
- (104) Widmer-Cooper, A.; Perry, H.; Harrowell, P.; Reichman, D. R. Irreversible reorganization in a supercooled liquid originates from localized soft modes. *Nat. Phys.* **2008**, *4*, 711.
- (105) Tanguy, A.; Mantsi, B.; Tsamados, M. Vibrational modes as a predictor for plasticity in a model glass. *Europhys. Lett.* **2010**, *90*, No. 16004.
- (106) Manning, M. L.; Liu, A. J. Vibrational modes identify soft spots in a sheared disordered packing. *Phys. Rev. Lett.* **2011**, *107*, No. 108302.
- (107) Lerner, E.; Bouchbinder, E. Low-energy quasilocated excitations in structural glasses. *J. Chem. Phys.* **2021**, *155*, No. 200901.
- (108) Wu, Z. W.; Chen, Y.; Wang, W.-H.; Kob, W.; Xu, L. Topology of vibrational modes predicts plastic events in glasses. *Nat. Commun.* **2023**, *14*, 2955.
- (109) Kapteijns, G.; Richard, D.; Lerner, E. Nonlinear quasilocated excitations in glasses: True representatives of soft spots. *Phys. Rev. E* **2020**, *101*, No. 032130.
- (110) Jack, R. L.; Dunleavy, A. J.; Royall, C. P. Information-theoretic measurements of coupling between structure and dynamics in glass formers. *Phys. Rev. Lett.* **2014**, *113*, No. 095703.
- (111) Mizuno, H.; Shimada, M.; Ikeda, A. Anharmonic properties of vibrational excitations in amorphous solids. *Phys. Rev. Res.* **2020**, *2*, No. 013215.
- (112) Li, Y.-W.; Yao, Y.; Ciamarra, M. P. Local plastic response and slow heterogeneous dynamics of supercooled liquids. *Phys. Rev. Lett.* **2022**, *128*, No. 258001.

- (113) Picard, G.; Ajdari, A.; Lequeux, F.; Bocquet, L. Elastic consequences of a single plastic event: A step towards the microscopic modeling of the flow of yield stress fluids. *Eur. J. Phys. E* **2004**, *15*, 371.
- (114) Chikkadi, V.; Wegdam, G.; Bonn, D.; Nienhuis, B.; Schall, P. Long-range strain correlations in sheared colloidal glasses. *Phys. Rev. Lett.* **2011**, *107*, No. 198303.
- (115) Chowdhury, S.; Abraham, S.; Hudson, T.; Harrowell, P. Long range stress correlations in the inherent structures of liquids at rest. *J. Chem. Phys.* **2016**, *144*, No. 124508.
- (116) Buchenau, U. Eshelby description of highly viscous flow – Half model, half theory. *J. Chem. Phys.* **2018**, *149*, No. 044508.
- (117) Hasyim, M. R.; Mandadapu, K. K. A theory of localized excitations in supercooled liquids. *J. Chem. Phys.* **2021**, *155*, No. 044504.
- (118) Flenner, E.; Szamel, G. Long-range spatial correlations of particle displacements and the emergence of elasticity. *Phys. Rev. Lett.* **2015**, *114*, No. 025501.
- (119) Maier, M.; Zippelius, A.; Fuchs, M. Emergence of long-ranged stress correlations at the liquid to glass transition. *Phys. Rev. Lett.* **2017**, *119*, No. 265701.
- (120) Klochko, L.; Baschnagel, J.; Wittmer, J. P.; Meyer, H.; Benzerara, O.; Semenov, A. N. Theory of length-scale dependent relaxation moduli and stress fluctuations in glass-forming and viscoelastic liquids. *J. Chem. Phys.* **2022**, *156*, No. 164505.
- (121) Steffen, D.; Schneider, L.; Müller, M.; Rottler, J. Molecular simulations and hydrodynamic theory of nonlocal shear-stress correlations in supercooled fluids. *J. Chem. Phys.* **2022**, *157*, No. 064501.
- (122) Wei, D.; Yang, J.; Jiang, M.-Q.; Dai, L.-H.; Wang, Y.-J.; Dyre, J. C.; Douglass, I.; Harrowell, P. Assessing the utility of structure in amorphous materials. *J. Chem. Phys.* **2019**, *150*, No. 114502.
- (123) Hurley, M. M.; Harrowell, P. Kinetic structure of a two-dimensional liquid. *Phys. Rev. E* **1995**, *52*, 1694.
- (124) Schiener, B.; Böhmer, R.; Loidl, A.; Chamberlin, R. V. Nonresonant spectral hole burning in the slow dielectric response of supercooled liquids. *Science* **1996**, *274*, 752.
- (125) Glotzer, S. C. Spatially heterogeneous dynamics in liquids: insights from simulation. *J. Non-Cryst. Solids* **2000**, *274*, 342.
- (126) Berthier, L. Self-induced heterogeneity in deeply supercooled liquids. *Phys. Rev. Lett.* **2021**, *127*, No. 088002.
- (127) Diezemann, G. A free-energy landscape model for primary relaxation in glass-forming liquids: Rotations and dynamic heterogeneities. *J. Chem. Phys.* **1997**, *107*, No. 10112.
- (128) Ciamarra, M. P.; Ji, W.; Wyart, M. The energy cost of local rearrangements, not cooperative effects, makes glasses solids. *arXiv*, arXiv:2302.05150v1, 2023. .
- (129) Wolynes, P. G.; Lubchenko, V. *Structural Glasses and Supercooled Liquids: Theory, Experiment, and Applications*; Wiley: New York, 2012.
- (130) Parisi, G.; Urbani, P.; Zamponi, F. *Theory of Simple Glasses*; Cambridge University Press, 2020.
- (131) Santen, L.; Krauth, W. Absence of thermodynamic phase transition in a model glass former. *Nature* **2000**, *405*, 550.
- (132) Ninarello, A.; Berthier, L.; Coslovich, D. Models and algorithms for the next generation of glass transition studies. *Phys. Rev. X* **2017**, *7*, No. 021039.
- (133) Gavazzoni, C.; Brito, C.; Wyart, M. Testing theories of the glass transition with the same liquid, but many kinetic rules. *arXiv*, arXiv:2308.00196, 2023. .
- (134) Tahaei, A.; Biroli, G.; Ozawa, M.; Popovic, M.; Wyart, M. Scaling description of dynamical heterogeneity and avalanches of relaxation in glass-forming liquids. *Phys. Rev. X* **2023**, *13*, No. 031034.
- (135) Ozawa, M.; Biroli, G. Elasticity, facilitation, and dynamic heterogeneity in glass-forming liquids. *Phys. Rev. Lett.* **2023**, *130*, No. 138201.
- (136) Hecksher, T.; Nielsen, A. I.; Olsen, N. B.; Dyre, J. C. Little evidence for dynamic divergences in ultraviscous molecular liquids. *Nat. Phys.* **2008**, *4*, 737.
- (137) McKenna, G. B.; Zhao, J. Accumulating evidence for non-diverging time-scales in glass-forming fluids. *J. Non-Cryst. Solids* **2015**, *407*, 3.
- (138) Fredrickson, G. H.; Andersen, H. C. Kinetic Ising model of the glass transition. *Phys. Rev. Lett.* **1984**, *53*, 1244.
- (139) Garrahan, J. P.; Chandler, D. Geometrical explanation and scaling of dynamical heterogeneities in glass forming systems. *Phys. Rev. Lett.* **2002**, *89*, No. 035704.
- (140) Ritort, F.; Sollich, P. Glassy dynamics of kinetically constrained models. *Adv. Phys.* **2003**, *52*, 219.
- (141) Zhang, G.; Xiao, H.; Yang, E.; Ivancic, R. J. S.; Ridout, S. A.; Riggleman, R. A.; Durian, D. J.; Liu, A. J. Structuro-elasto-plasticity model for large deformation of disordered solids. *Phys. Rev. Res.* **2022**, *4*, No. 043026.
- (142) Schmidt-Rohr, K.; Spiess, H. W. Nature of nonexponential loss of correlation above the glass transition investigated by multidimensional NMR. *Phys. Rev. Lett.* **1991**, *66*, 3020.
- (143) Duan, J.; Wang, Y. J.; Dai, L. H.; Jiang, M. Q. Elastic interactions of plastic events in strained amorphous solids before yield. *Phys. Rev. Mater.* **2023**, *7*, No. 013601.
- (144) Shang, B.; Guan, P.; Barrat, J.-L. Elastic avalanches reveal marginal behavior in amorphous solids. *Proc. Natl. Acad. Sci. U.S.A.* **2020**, *117*, 86.
- (145) Richard, D.; Elgailani, A.; Vandembroucq, D.; Manning, M. L.; Maloney, C. E. Mechanical excitation and marginal triggering during avalanches in sheared amorphous solids. *Phys. Rev. E* **2023**, *107*, No. 034902.
- (146) Scalliet, C.; Guiselin, B.; Berthier, L. Excess wings and asymmetric relaxation spectra in a facilitated trap model. *J. Chem. Phys.* **2021**, *155*, No. 064505.
- (147) Hasyim, M. R.; Mandadapu, K. K. Emergent facilitation and glassy dynamics in supercooled liquids. *arXiv*, arXiv:2310.06584, 2023. .
- (148) Ridout, S. A.; Tah, I.; Liu, A. J. Building a “trap model” of glassy dynamics from a local structural predictor of rearrangements. *Europhys. Lett.* **2023**, *144*, 47001.
- (149) Reichl, L. E. *A Modern Course in Statistical Physics*, 4th ed.; Wiley-VCH, 2016.
- (150) Johari, G. P.; Goldstein, M. Viscous liquids and the glass transition. II. Secondary relaxations in glasses of rigid molecules. *J. Chem. Phys.* **1970**, *53*, 2372.
- (151) Stauffer, D.; Aharony, A. *Introduction To Percolation Theory*, 2nd ed. Routledge, 1992.
- (152) Isichenko, M. B. Percolation, statistical topography, and transport in random media. *Rev. Mod. Phys.* **1992**, *64*, 961.
- (153) Douglass, I. M.; Dyre, J. C. Distance-as-time in physical aging. *Phys. Rev. E* **2022**, *106*, No. 054615.
- (154) Chang, I.; Sillescu, H. Heterogeneity at the glass transition: Translational and rotational self-diffusion. *J. Phys. Chem. B* **1997**, *101*, 8794.
- (155) Yamamoto, R.; Onuki, A. Heterogeneous diffusion in highly supercooled liquids. *Phys. Rev. Lett.* **1998**, *81*, 4915.
- (156) Richert, R.; Böhmer, R. Heterogeneous and homogeneous diffusivity in an ion-conducting glass. *Phys. Rev. Lett.* **1999**, *83*, 4337.
- (157) Xu, X.; Douglas, J. F.; Xu, W.-S. Parallel emergence of rigidity and collective motion in a family of simulated glass-forming polymer fluids. *Macromolecules* **2023**, *56*, 4929.
- (158) Stillinger, F. H. Relaxation and flow mechanisms in “fragile” glass-forming liquids. *J. Chem. Phys.* **1988**, *89*, 6461.
- (159) Kumar, S. K.; Szamel, G.; Douglas, J. F. Nature of the breakdown in the Stokes-Einstein relationship in a hard sphere fluid. *J. Chem. Phys.* **2006**, *124*, No. 214501.
- (160) Szamel, G.; Flenner, E. Time scale for the onset of Fickian diffusion in supercooled liquids. *Phys. Rev. E* **2006**, *73*, No. 011504.
- (161) Higler, R.; Krausser, J.; van der Gucht, J.; Zaccone, A.; Sprakel, J. Linking slow dynamics and microscopic connectivity in dense suspensions of charged colloids. *Soft Matter* **2018**, *14*, 780.

- (162) Guiselin, B.; Scalliet, C.; Berthier, L. Microscopic origin of excess wings in relaxation spectra of supercooled liquids. *Nat. Phys.* **2022**, *18*, 468.
- (163) Scalliet, C.; Guiselin, B.; Berthier, L. Thirty milliseconds in the life of a supercooled liquid. *Phys. Rev. X* **2022**, *12*, No. 041028.
- (164) Gao, L.; Sun, Y.; Yu, H.-B. Mobility percolation as a source of Johari-Goldstein relaxation in glasses. *Phys. Rev. B* **2023**, *108*, No. 014201.
- (165) Donati, C.; Douglas, J. F.; Kob, W.; Plimpton, S. J.; Poole, P. H.; Glotzer, S. C. Stringlike cooperative motion in a supercooled liquid. *Phys. Rev. Lett.* **1998**, *80*, 2338.
- (166) Russina, M.; Mezei, F.; Lechner, R.; Longeville, S.; Urban, B. Experimental evidence for fast heterogeneous collective structural relaxation in a supercooled liquid near the glass transition. *Phys. Rev. Lett.* **2000**, *84*, 3630.
- (167) Long, D.; Lequeux, F. Heterogeneous dynamics at the glass transition in van der Waals liquids, in the bulk and in thin films. *Eur. Phys. J. E* **2001**, *4*, 371.
- (168) Stevenson, J. D.; Wolynes, P. G. A universal origin for secondary relaxations in supercooled liquids and structural glasses. *Nat. Phys.* **2010**, *6*, 62.
- (169) Starr, F. W.; Douglas, J. F.; Sastry, S. The relationship of dynamical heterogeneity to the Adam-Gibbs and random first-order transition theories of glass formation. *J. Chem. Phys.* **2013**, *138*, 12A541.
- (170) Cicerone, M. T.; Zhong, Q.; Tyagi, M. Picosecond dynamic heterogeneity, hopping, and Johari-Goldstein relaxation in glass-forming liquids. *Phys. Rev. Lett.* **2014**, *113*, No. 117801.
- (171) Yu, H.-B.; Richert, R.; Samwer, K. Structural rearrangements governing Johari-Goldstein relaxations in metallic glasses. *Sci. Adv.* **2017**, *3*, No. e1701577.
- (172) Pazmino Betancourt, B. A.; Starr, F. W.; Douglas, J. F. Stringlike collective motion in the α - and β -relaxation of a coarse-grained polymer melt. *J. Chem. Phys.* **2018**, *148*, No. 104508.
- (173) Caporaletti, F.; Capaccioli, S.; Valenti, S.; Mikolasek, M.; Chumakov, A. I.; Monaco, G. A microscopic look at the Johari-Goldstein relaxation in a hydrogen-bonded glass-former. *Sci. Rep.* **2019**, *9*, No. 14319.
- (174) Caporaletti, F.; Capaccioli, S.; Valenti, S.; Mikolasek, M.; Chumakov, A. I.; Monaco, G. Experimental evidence of mosaic structure in strongly supercooled molecular liquids. *Nat. Commun.* **2021**, *12*, 1867.
- (175) Chang, C.; Zhang, H. P.; Zhao, R.; Li, F. C.; Luo, P.; Li, M. Z.; Bai, H. Y. Liquid-like atoms in dense-packed solid glasses. *Nat. Mater.* **2022**, *21*, 1240.
- (176) Spieckermann, F.; Söpu, D.; Soprunyuk, V.; Kerber, M. B.; Bednarcik, J.; Schökel, A.; Rezvan, A.; Ketov, S.; Sarac, B.; Schafner, E.; Eckert, J. Structure-dynamics relationships in cryogenically deformed bulk metallic glass. *Nat. Commun.* **2022**, *13*, 127.
- (177) Novikov, V. N.; Rössler, E.; Malinovsky, V. K.; Surovtsev, N. V. Strong and fragile liquids in percolation approach to the glass transition. *Europhys. Lett.* **1996**, *35*, 289.
- (178) Kob, W. *personal communication*, 2023.
- (179) Ghosh, A.; Budrikis, Z.; Chikkadi, V.; Sellerio, A. L.; Zapperi, S.; Schall, P. Direct observation of percolation in the yielding transition of colloidal glasses. *Phys. Rev. Lett.* **2017**, *118*, No. 148001.
- (180) Olsen, N. B. Scaling of β -relaxation in the equilibrium liquid state of sorbitol. *J. Non-Cryst. Solids* **1998**, *235*, 399.
- (181) Schneider, U.; Brand, R.; Lunkenheimer, P.; Loidl, A. Excess wing in the dielectric loss of glass formers: A Johari-Goldstein β relaxation? *Phys. Rev. Lett.* **2000**, *84*, 5560.
- (182) Nielsen, A. I.; Christensen, T.; Jakobsen, B.; Niss, K.; Olsen, N. B.; Richert, R.; Dyre, J. C. Prevalence of approximate relaxation for the dielectric α process in viscous organic liquids. *J. Chem. Phys.* **2009**, *130*, No. 154508.
- (183) Pabst, F.; Gabriel, J. P.; Böhmer, T.; Weigl, P.; Helbling, A.; Richter, T.; Zourchang, P.; Walther, T.; Blochowicz, T. Generic structural relaxation in supercooled liquids. *J. Phys. Chem. Lett.* **2021**, *12*, 3685.
- (184) Sidebottom, D. L. Generic α relaxation in a strong GeO₂ glass melt. *Phys. Rev. E* **2023**, *107*, L012602.
- (185) Kittel, C. *Introduction to Solid State Physics*, 5th ed.; Wiley: New York, 1976.
- (186) Flynn, C. P. Atomic migration in monatomic crystals. *Phys. Rev.* **1968**, *171*, 682.
- (187) Rouxel, T. Thermodynamics of viscous flow and elasticity of glass forming liquids in the glass transition range. *J. Chem. Phys.* **2011**, *135*, No. 184501.
- (188) Pazmino Betancourt, B. A.; Hanakata, P. Z.; Starr, F. W.; Douglas, J. F. Quantitative relations between cooperative motion, emergent elasticity, and free volume in model glass-forming polymer materials. *Proc. Natl. Acad. Sci. U.S.A.* **2015**, *112*, 2966.
- (189) Mirigian, S.; Schweizer, K. S. Elastically cooperative activated barrier hopping theory of relaxation in viscous fluids. I. General formulation and application to hard sphere fluids. *J. Chem. Phys.* **2014**, *140*, No. 194506.
- (190) Phan, A.; Schweizer, K. S. Elastically collective nonlinear Langevin equation theory of glass-forming liquids: Transient localization, thermodynamic mapping, and cooperativity. *J. Phys. Chem. B* **2018**, *122*, 8451.
- (191) Mei, B.; Zhou, Y.; Schweizer, K. S. Experimental test of a predicted dynamics–structure–thermodynamics connection in molecularly complex glass-forming liquids. *Proc. Natl. Acad. Sci. U.S.A.* **2021**, *118*, No. e2025341118.
- (192) Dyre, J. C. A model for the generic alpha relaxation of viscous liquids. *Europhys. Lett.* **2005**, *71*, 646.
- (193) Dyre, J. C.; Olsen, N. B.; Christensen, T. Local elastic expansion model for viscous-flow activation energies of glass-forming molecular liquids. *Phys. Rev. B* **1996**, *53*, 2171.
- (194) Hecksher, T.; Dyre, J. C. A review of experiments testing the shoving model. *J. Non-Cryst. Solids* **2015**, *407*, 14.
- (195) Dyre, J. C. Dominance of shear elastic energy far from a point defect in a solid. *Phys. Rev. B* **2007**, *75*, No. 092102.
- (196) Varotsos, P. A.; Alexopoulos, K. D. *Thermodynamics of Point Defects and their Relation with Bulk Properties*; North-Holland: Amsterdam, 1986.
- (197) Hall, R. W.; Wolynes, P. G. The aperiodic crystal picture and free energy barriers in glasses. *J. Chem. Phys.* **1987**, *86*, 2943.
- (198) Larini, L.; Ottochian, A.; De Michele, C.; Leporini, D. Universal scaling between structural relaxation and vibrational dynamics in glass-forming liquids and polymers. *Nat. Phys.* **2008**, *4*, 42.
- (199) Ding, J.; Cheng, Y.-Q.; Sheng, H.; Asta, M.; Ritchie, R. O.; Ma, E. Universal structural parameter to quantitatively predict metallic glass properties. *Nat. Comm.* **2016**, *7*, No. 13733.
- (200) Lovi, J. M.; Sen, S. Effects of the 10B/11B isotopic substitution on shear relaxation in supercooled B₂O₃ liquid: A validation of the elastic model of viscous flow. *J. Chem. Phys.* **2023**, *158*, No. 141103.
- (201) Dudowicz, J.; Freed, K. F.; Douglas, J. F. The glass transition temperature of polymer melts. *J. Phys. Chem. B* **2005**, *109*, No. 21285.
- (202) Pedersen, U. R.; Costigliola, L.; Bailey, N. P.; Schröder, T. B.; Dyre, J. C. Thermodynamics of freezing and melting. *Nat. Commun.* **2016**, *7*, No. 12386.
- (203) Lunkenheimer, P.; Loidl, A.; Riechers, B.; Zaccone, A.; Samwer, K. Thermal expansion and the glass transition. *Nat. Phys.* **2023**, *19*, 694.
- (204) Dyre, J. C.; Olsen, N. B. Landscape equivalent of the shoving model. *Phys. Rev. E* **2004**, *69*, No. 042501.
- (205) Wang, J. Q.; Wang, W. H.; Liu, Y. H.; Bai, H. Y. Characterization of activation energy for flow in metallic glasses. *Phys. Rev. B* **2011**, *83*, No. 012201.
- (206) Dyre, J. C.; Wang, W. H. The instantaneous shear modulus in the shoving model. *J. Chem. Phys.* **2012**, *136*, No. 224108.
- (207) Scopigno, T.; Ruocco, G.; Sette, F.; Monaco, G. Is the fragility of a liquid embedded in the properties of its glass? *Science* **2003**, *302*, 849.

- (208) Veldhorst, A. A.; Ribeiro, M. C. C. Mechanical heterogeneity in ionic liquids. *J. Chem. Phys.* **2018**, *148*, No. 193803.
- (209) Shang, B.; Rottler, J.; Guan, P.; Barrat, J.-L. Local versus global stretched mechanical response in a supercooled liquid near the glass transition. *Phys. Rev. Lett.* **2019**, *122*, No. 105501.
- (210) Weigl, P.; Hecksher, T.; Dyre, J. C.; Walther, T.; Blochowicz, T. Identity of the local and macroscopic dynamic elastic responses in supercooled 1-propanol. *Phys. Chem. Chem. Phys.* **2021**, *23*, No. 16537.
- (211) Kapteijns, G.; Richard, D.; Bouchbinder, E.; Schröder, T. B.; Dyre, J. C.; Lerner, E. Does mesoscopic elasticity control viscous slowing down in glassforming liquids? *J. Chem. Phys.* **2021**, *155*, No. 074502.
- (212) Dyre, J. C. Source of non-Arrhenius average relaxation time in glass-forming liquids. *J. Non-Cryst. Solids* **1998**, *235*, 142.
- (213) Mirigian, S.; Schweizer, K. S. Unified theory of activated relaxation in liquids over 14 decades in time. *J. Phys. Chem. Lett.* **2013**, *4*, 3648.
- (214) Torchinsky, D. H.; Johnson, J. A.; Nelson, K. A. A direct test of the correlation between elastic parameters and fragility of ten glass formers and their relationship to elastic models of the glass transition. *J. Chem. Phys.* **2009**, *130*, No. 064502.
- (215) Flenner, E.; Szamel, G. Fundamental differences between glassy dynamics in two and three dimensions. *Nat. Commun.* **2015**, *6*, 7392.
- (216) Berthier, L.; Charbonneau, P.; Ninarello, A.; Ozawa, M.; Yaida, S. Zero-temperature glass transition in two dimensions. *Nat. Commun.* **2019**, *10*, 1508.
- (217) Vila-Costa, A.; Gonzalez-Silveira, M.; Rodriguez-Tinoco, C.; Rodriguez-Lopez, M.; Rodriguez-Viejo, J. Emergence of equilibrated liquid regions within the glass. *Nat. Phys.* **2023**, *19*, 114.
- (218) Kong, D.; Chen, W.-R.; Zeng, K.-Q.; Porcar, L.; Wang, Z. Localized elasticity governs the nonlinear rheology of colloidal supercooled liquids. *Phys. Rev. X* **2022**, *12*, No. 041006.
- (219) Vogel, F.; Zippelius, A.; Fuchs, M. Emergence of Goldstone excitations in stress correlations of glass-forming colloidal dispersions. *Europhys. Lett.* **2019**, *125*, No. 68003.
- (220) Herrero, C.; Scalliet, C.; Ediger, M. D.; Berthier, L. Two-step devitrification of ultrastable glasses. *Proc. Natl. Acad. Sci. U.S.A.* **2023**, *120*, No. e2220824120.
- (221) Karimi, K.; Alava, M. J.; Papanikolaou, S. Yielding in multicomponent metallic glasses: Universal signatures of elastic modulus heterogeneities. *Phys. Rev. Mater.* **2023**, *7*, No. 063601.
- (222) Schröder, T. B.; Dyre, J. C. ac hopping conduction at extreme disorder takes place on the percolating cluster. *Phys. Rev. Lett.* **2008**, *101*, No. 025901.
- (223) Schröder, T. B.; Dyre, J. C. Solid-like mean-square displacement in glass-forming liquids. *J. Chem. Phys.* **2020**, *152*, No. 141101.
- (224) Bierwirth, S. P.; Böhmer, R.; Gainaru, C. Generic primary mechanical response of viscous liquids. *Phys. Rev. Lett.* **2017**, *119*, No. 248001.